

## Critical current density and magnetization studies on Bi(Pb)SrCaCuO

P K MISHRA, SHAILENDRA KUMAR, G RAVIKUMAR, P CHADDAH, B A DASANNACHARYA, RAM PRASAD\* and N C SONI\*

Nuclear Physics Division, \*Metallurgy Division, Bhabha Atomic Research Centre, Bombay 400085, India.

**Abstract.** High  $T_c$  phase ( $T_c \sim 110$  K) has been obtained in Bi–Sr–Ca–Cu–O system by partially substituting Bi by Pb. Magnetic hysteresis has been measured as a function of temperature. Critical current densities have been measured at 77 K both by transport and a.c. magnetization method in bulk samples for various concentrations of Pb. The results show that substitution of 15 at% Pb for Bi is most preferable for higher critical current density.

**Keywords.** Critical current; superconductivity; magnetization measurements.

### 1. Introduction

Following the discovery of superconductivity in Bi–Sr–Ca–Cu–O system (Michel *et al* 1987; Maeda *et al* 1988), it is well established that the compound exhibits superconductivity in two phases, viz. a high  $T_c$  2223 phase ( $T_c \sim 110$  K) and a low  $T_c$  2212 phase ( $T_c \sim 80$  K). The two phases are normally found to coexist, so that the zero resistance is attained only below 85 K.

Efforts have been made to stabilize the high  $T_c$  (110 K) phase by different methods. Limited success has been obtained (Shi *et al* 1988) in pure compounds to achieve  $\rho = 0$  at 110 K. The procedure involves long sintering times and is complicated. An alternative approach (Statt *et al* 1988) is to dope Pb for bismuth which aids the growth of 110 K phase. The latter procedure is more common for its simplicity, but is believed to result in multi-phase samples. In this paper we present our studies on critical current densities and low field magnetization hysteresis in  $\text{Bi}_{2-x}\text{Pb}_x\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_y$  samples for  $0.2 \leq x \leq 0.4$ .

### 2. Experimental details and results

Samples were prepared by reaction (Tomy *et al* 1989) of  $\text{Bi}_2\text{O}_3$ , PbO and  $\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_7$  with two different types of heat treatments. In the first type (referred to as group I), the mixture was calcined in air at 820°C for 2 h, then pelletized and sintered at 855°C for 96 h in air and then slow-cooled. For the other group (referred to as group II), the mixture was first pressed and flashed to 900°C for 5 min for surface-melting followed by sintering at 855°C for 96 h in air and then slow-cooled.

Transport measurements of  $J_c$  were made (Malik *et al* 1988) at 77 K from the V–I curve. The results are shown in table 1. We note that  $J_c$  value is lower than that

obtained in YBaCuO system. A peak in  $J_c$  is obtained for  $x = 0.3$  for both groups of samples without any significant change in  $T_c$ .

The hysteresis curves are measured using an AC (317 Hz) susceptibility instrument (Radhakrishnamurthy *et al* 1978) coupled with a flow-type liquid nitrogen cryostat. The sample and a copper constantan thermocouple are encapsulated in a nylon sample holder which is filled with Apiezone N grease. The sample holder rests in a glass tube and its position is adjustable with respect to the secondary coils of the susceptibility instrument. Temperature is varied in the range of  $T = 77$  K to 120 K with  $\Delta T = \pm 0.5$  K by controlling the rate of flow of the nitrogen gas through liquid nitrogen. Samples in the pellet geometry are used in this study. The maximum cycling field,  $H_{\max}$ , can be varied between 1 Gauss and 10 Gauss.  $T_c$  was measured as the temperature of diamagnetic onset with a cycling field  $H_{\max} = 8$  Gauss.  $J_c$  can also be estimated from the remnant magnetization  $M_r$  at 77 K in the field of 8 Gauss. The remnant magnetization is indicated schematically in figure 1 and gives a measure of the transport  $J_c$  (Shailendra Kumar *et al* 1990). The data obtained from the low field hysteresis are shown in table 2.

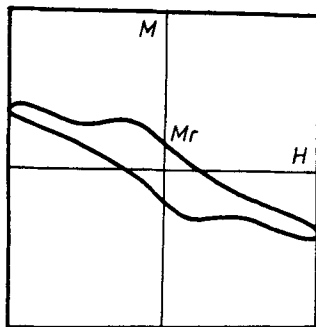


Figure 1. Schematic of hysteresis curve for  $H_{\max} = 8$  Gauss at 77 K.

Table 1. Transport  $J_c$  and  $T_c$  of various samples.

$x$	Gr. I. $J_c$ (amp/cm <sup>2</sup> )	$T_c$ (K)	Gr. II. $J_c$ (amp/cm <sup>2</sup> )	$T_c$ (K)
0.2	0.70	110	Very small	108
0.3	12.30	110	6.86	110
0.4	1.40	108	3.62	110

Table 2. Remnant magnetization  $M_r$  for different concentrations of Pb.

$x$	Gr. I. $2M_r$ (arbitrary unit)	Gr. II. $2M_r$ (arbitrary unit)
0.2	0.0	1.0
0.3	11.5	4.5
0.4	8.5	2.0

$M_r$  also peaks at  $x = 0.3$  and this correlates qualitatively with the transport measurement.

### 3. Conclusion

The transport  $J_c$  measured from the V-I curve shows a clear peak at  $x = 0.3$  irrespective of the preparation route followed, while  $T_c$  (as measured from the diamagnetic onset) is unchanged (to within 2 K) as  $x$  is varied from 0.2 to 0.4. The stronger intergrain coupling at  $x = 0.3$  is also reflected in the fact that  $M_r$  peaks at  $x = 0.3$ .

The addition of lead helps stabilize the 2223 phase and its concentration is not crucial for high  $T_c$ . Our results show that the best intergrain coupling is achieved for  $x = 0.3$ .

### References

- Maeda H, Tanaka Y, Fukutomi M and Asano T 1988 *Jpn J. Appl. Phys. Lett.* **27** L209
- Malik M K, Nair V D, Biswas A R, Raghavan R V, Chaddah P, Mishra P K, Ravi Kumar G and Dasannacharya B A 1988 *Appl. Phys. Lett.* **52** 1525
- Michel C, Hervieu M, Borel M M, Grandin A, Deslandes F, Provost J and Raveau B 1987 *Z. Phys.* **B68** 421
- Radhakrishnamurthy C, Likhite S D and Sahasrabudhe P W 1978 *Proc. Indian Acad. Sci.-Chem. Sci.* **A78** 245
- Shailendra Kumar, Ravikumar G, Mishra P K, Chaddah P, Dasannacharya B A, Ram Prasad and Soni N C 1990 *Presented at the Int. Conf. on Superconductivity* (to be published)
- Shi D, Blank M, Patel M, Hinks D G, Mitchell A W, Vandervoot K and Claus H 1988 *Physica* **C156** 822
- Statt B W, Wang Z, Lee M J G, Yakhmi J V, De Camargo P C, Major J F and Rutter J W 1988 *Physica* **C156** 251
- Tomy C V, Ram Prasad, Soni N C, Kalyan A and Malik S K 1989 Paper presented at M<sup>2</sup>S-HTSC, Stanford