

Microwave synthesis of electrode materials for lithium batteries

M HARISH BHAT, B P CHAKRAVARTHY, P A RAMAKRISHNAN, A LEVASSEUR[†]
and K J RAO*

Solid State and Structural Chemistry Unit, Indian Institute of Science, Bangalore 560 012, India

[†]ENSCP, Avenue Pey Berland, BP 108, 334 02, Talence Cedex, Bordeaux, France

MS received 7 November 2000

Abstract. A novel microwave method is described for the preparation of electrode materials required for lithium batteries. The method is simple, fast and carried out in most cases with the same starting material as in conventional methods. Good crystallinity has been noted and lower temperatures of reaction has been inferred in cases where low temperature products have been identified.

Keywords. Novel microwave method; electrode materials; lithium batteries.

1. Introduction

There has been an increasing interest in the development of Li batteries for the last two decades, owing primarily to the higher voltages and energy densities realizable in them. The problems of safety associated with the use of Li metal due to its chemical reactivity with the ambient and the problems of dendritic regrowth of Li on the anode upon cycling, which leads to short-circuiting of the cell, have been the major disadvantages of Li batteries. This is sought to be overcome by the introduction of a more advanced and inherently safe 'rocking chair' configuration of lithium batteries (so called because the Li ions rock back and forth between the two electrodes during charge/discharge cycles). Rocking chair batteries use insertion compounds as electrode materials for both the anode and the cathode (Murphy *et al* 1978; Murphy and Carides 1979; Lazzari and Scrosati 1980; Mizushima *et al* 1980). The output voltage of such cells is determined by the difference between the electrochemical potential of Li⁺ ions in the two electrochemical insertion compounds. It is implied that the cathode and anode should be compounds which can be intercalated with Li⁺ ions at high and low voltages respectively.

Intensive research on electrode materials has shown that for the negative electrode (anode), Li metal can be replaced effectively either by a Li–Al alloy (Peled *et al* 1983) or by intercalation materials based on carbon (Kanno *et al* 1989; Mohri *et al* 1989; Fong *et al* 1990). The loss in the voltage due to the Li⁺ potential in intercalated carbon compared to Li metal itself is compensated by the use of cathode materials with higher oxidation potentials. Some of the materials which meet this require-

ment are LiMn₂O₄ (Tarascon and Guyomard 1991, 1993; Guyomard and Tarascon 1992), LiCoO₂ (Thomas *et al* 1985; Gummow *et al* 1992) and LiNiO₂ (Dahn *et al* 1990, 1991; Ozawa 1994). In batteries employing glassy electrolytes, compounds like TiS₂, Cu₄O(PO₄)₂, CuBi₂O₄, Bi₄B₂O₉ have been used as cathodes (Jones and Akridge 1995). It has been found that in all these cases, the performance of the electrodes is significantly influenced by the method of their preparation. For example, samples synthesized at low temperatures show better cyclability but lower capacity than those prepared at higher temperatures. It is, therefore, necessary to develop methods of synthesis, which give rise to materials of better electrode characteristics and are also cheap and reproducible.

Use of microwaves for the synthesis of inorganic compounds has gained great importance in recent years (Mingos and Baghurst 1991; Rao and Ramesh 1995; Rao *et al* 1999). The method offers several advantages over the conventional routes, the most important of them being the very short reaction times and energy economy. Several microwave reactions are now known to occur at lower temperatures than in conventional methods. The rapidity of the reactions offers excellent condition for retention of metastable phases. This novel method has been found to result in better reaction yields and better structural uniformity of products (Rao *et al* 1999a) than conventional ceramic methods. Further, the microwave method is also very clean and non-polluting. The rapidity of the reactions offers excellent possibilities for stabilizing metastable phases. This novel method has been found to result in better reaction yields and better structural uniformity of products. In order to use the microwave route, it is desirable that at least one of the reactants should be a microwave susceptor. However, this limitation can be overcome by the use of a secondary susceptor, which is chemically inert with respect to the reactants of interest. A micro-

*Author for correspondence

wave susceptor like graphite, which is generally non-reactive, is a superb secondary heater (Vaidhyanathan *et al* 1997). Researches at our laboratory and elsewhere have demonstrated the use of microwaves in the synthesis of a wide variety of oxides (Vaidhyanathan *et al* 1997; Baghurst and Mingos 1988; Baghurst *et al* 1988; Kladnig and Horn 1990), chalcogenides (Whittaker and Mingos 1992; Landry and Barron 1993; Kniep 1993; Vaidhyanathan *et al* 1995), carbides (Clark *et al* 1991; Ahmad *et al* 1991; Ramesh *et al* 1994), nitrides (Kiggans *et al* 1991; Ramesh and Rao 1995; Vaidhyanathan and Rao 1997a), silicides (Vaidhyanathan and Rao 1997b), borides (Mingos and Baghurst 1992) and glasses (Vaidhyanathan *et al* 1994, 1998). Therefore, we consider it important to develop a microwave route to synthesize electrode materials and examine their electrode characteristics. Materials like LiMn_2O_4 , LiCoO_2 , CuBi_2O_4 and $\text{Bi}_4\text{B}_2\text{O}_9$ have potential application in Li batteries. We report here a microwave method for the synthesis of these materials.

2. Experimental

Oxides or carbonates and iodides were used as reactants for the preparation of the complex oxides. Amorphous carbon was used as a secondary heater in some cases. Stoichiometric amounts of the required high purity reactants (total weight = 5–10 g) were ground well in each case and exposed to microwave irradiation for about 5–10 min in silica crucibles kept inside a domestic microwave oven (Batliboy-Eddy, 2.45 GHz, 980 W) operating at the highest power level. In some cases, the reaction was interrupted at the end of every 2 min and the partially reacted mixtures were ground well again to ensure homogeneity. Product formation was confirmed by powder X-ray diffraction (Philips, Model PW1050/70, Cu- K_α radiation). The lattice parameters were calculated using least squares fitting of XRD reflections.

Preliminary electrochemical characterization was carried out for LiMn_2O_4 by configuring appropriate cell assembly. Electrodes were made by mixing the active material


with PVDF (binder) and acetylene black in the ratio 80 : 10 : 10 by weight and pressing them as pellets. The pellets were heated to 175°C and were pressed once again at that temperature. A liquid electrolyte ($\text{LiClO}_4 + \text{EC} + \text{DEC}$) was used and was separated using polypropylene.

3. Results and discussion

3.1 LiMn_2O_4

The microwave preparation of lithium manganate was first attempted with Li_2CO_3 and MnO_2 as reactants. But the expected cubic spinel phase of LiMn_2O_4 was not formed. Instead a mixed phase of defect spinels of $\text{Li}_2\text{O}-y\text{MnO}_2$ was found to form. This in itself is quite interesting because the defect spinel is reported to be stable only below 400°C and upon heating above 400°C, it transforms to the cubic spinel. Therefore, the metastable phase seems to get stabilized easily in microwave preparation. This may be due to low microwave susceptibility of MnO_2 , which does not enable the system to attain high (> 400°C) temperature. The temperatures could not be measured in these experiments.

An alternate reaction scheme was used for the microwave preparation of the cubic spinel phase. An intimate mixture of LiI and MnO_2 was irradiated by microwaves. It was found that cubic spinel was formed directly in a single heating step of 6 min. The other product was iodine, which was in the gaseous phase and it provided an antioxidative shroud around the reaction mixture



Lattice parameter, a , of the cubic spinel phase was calculated by least squares fitting and found to be 8.244 Å. This value agrees very well with that reported in the literature ($a = 8.2476$ Å) [JCPDS, File No. 35-782]. The XRD pattern is shown in figure 1. The crystallinity of the product appears to be poor. The low microwave susceptibility of MnO_2 appears to limit the temperature attained by the


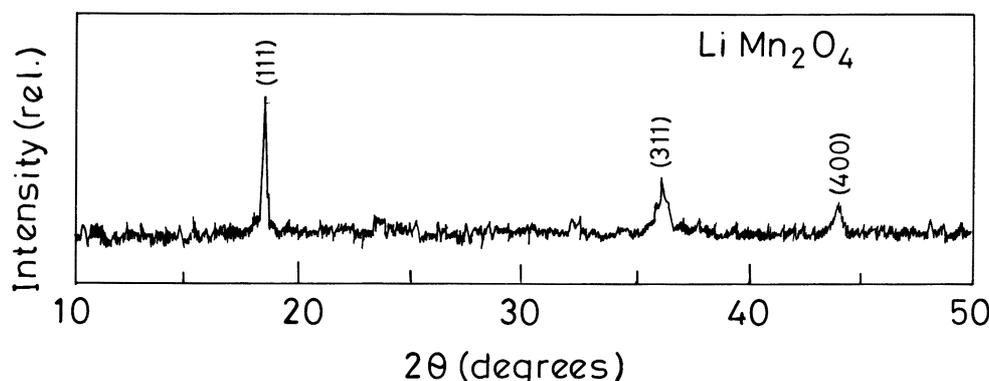


Figure 1. Powder X-ray diffraction pattern of microwave prepared cubic spinel, LiMn_2O_4 .

reactants. Also the reaction does not appear to be highly exothermic. As a consequence the temperature attained appears insufficient for achieving good crystallinity.


Alternately, LiMn_2O_4 was prepared by using stoichiometric quantities of Li_2CO_3 and MnO_2 , but by embedding a pellet of the mixture in amorphous carbon (used as a secondary heater) before irradiating with microwaves. The reaction was found to be completed in about 7 min of continuous irradiation and a cubic spinel of LiMn_2O_4 was found to form:



However, the high temperature attained during the synthesis (since amorphous carbon is used as secondary heater) results in the formation of fine powders with somewhat poor crystallinity.

LiMn_2O_4 of spinel structure possesses cathode reversibility of intercalated Li^+ ions above 4 V. Also, LiMn_2O_4 is not moisture sensitive and can be handled in ambient atmosphere. In comparison with the layered materials like LiCoO_2 and LiNiO_2 , LiMn_2O_4 is cheaper and environmentally benign. Formation of spinel lithium manganate is very sensitive to preparative conditions. The conventional method of preparation of LiMn_2O_4 involved solid state reaction of Li_2CO_3 and Mn_2O_3 above 1150 K. Alternate synthetic routes based on precursor (Huang and Bruce 1994, 1995) and sol-gel (Barboux *et al* 1991) methods have also been reported. Microwave method described above is therefore, clearly faster, cleaner and economical than other methods.

A preliminary electrochemical characterization has been performed using two different anodes ($\text{Li}_{0.3}\text{V}_2\text{O}_5$ and graphitic carbon) having the configuration



Batteries fabricated using $\text{Li}_{0.3}\text{V}_2\text{O}_5$ and LiMn_2O_4 as electrodes showed low voltages as well as low capacities (figure 2a). Note here that the $\text{Li}_{0.3}\text{V}_2\text{O}_5$ used was also prepared by a microwave method reported elsewhere (Rao *et al* 1999b). The low voltage of this battery is due to the small difference in the potentials of the electrode materials (w.r.t. Li). The expected voltages being $E \approx 3.4$ V for $\text{Li}_{0.3}\text{V}_2\text{O}_5/\text{Li}$ and $E \approx 4.2$ V for $\text{LiMn}_2\text{O}_4/\text{Li}$.

Poor intercalatability of Li into the electrode materials results in low capacity. When graphitic carbon was used as an anode instead of $\text{Li}_{0.3}\text{V}_2\text{O}_5$ in the above cell, the voltage was about 3.8 V but the capacity was not very high (figure 2b). Further studies are in progress.

3.2 LiCoO_2

The layered lithium cobaltate is an important cathode material and has been employed in the commercial batteries

manufactured by Sony Energytec (Nagaura 1990). This material was prepared from LiOH and $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ by mixing them in distilled water in 4 : 1 molar ratio (LiOH taken in excess). The solution was microwave irradiated for 10 min in order to remove the water. Since neither of the reactant is a microwave susceptor, the temperature did not rise further. The product formed at this stage was amorphous. The sample was heated at 973°C for 60 min and X-ray pattern showed the formation of poorly crystalline LiCoO_2 (figure 3a). Alternately, Li_2CO_3 and $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ were ground into a pellet and embedded

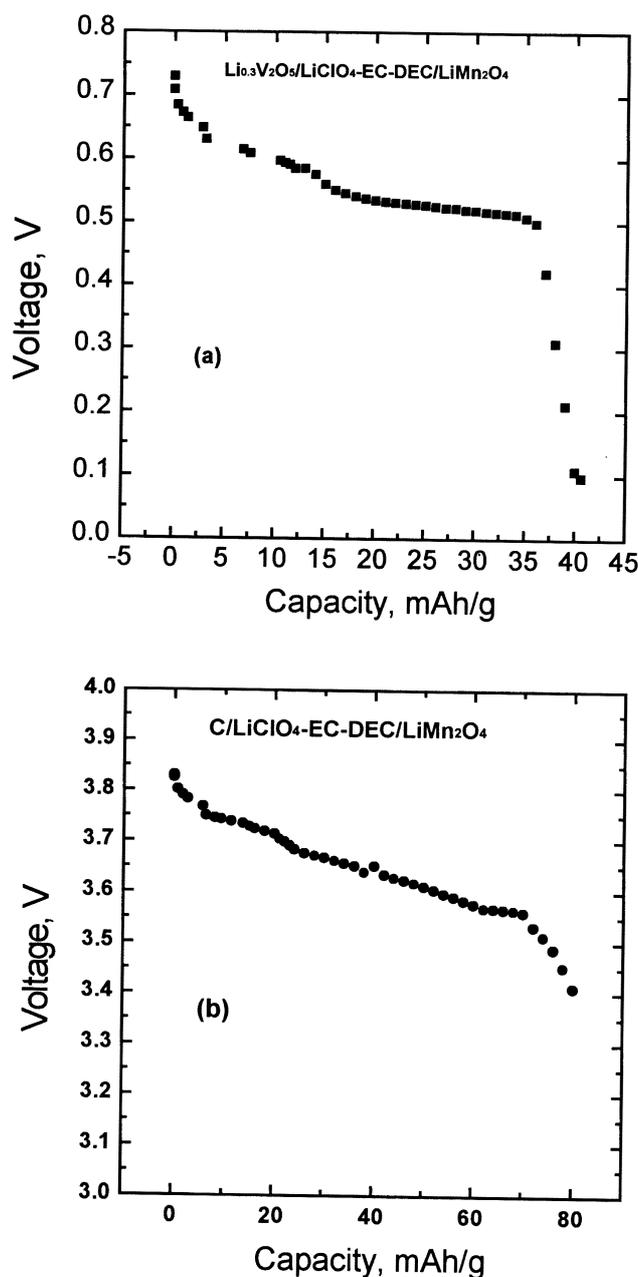


Figure 2. Discharge characteristics of LiMn_2O_4 using the anodes (a) $\text{Li}_{0.3}\text{V}_2\text{O}_5$ and (b) graphitic carbon, discharged at a constant current of 0.2 mA/cm^2 .

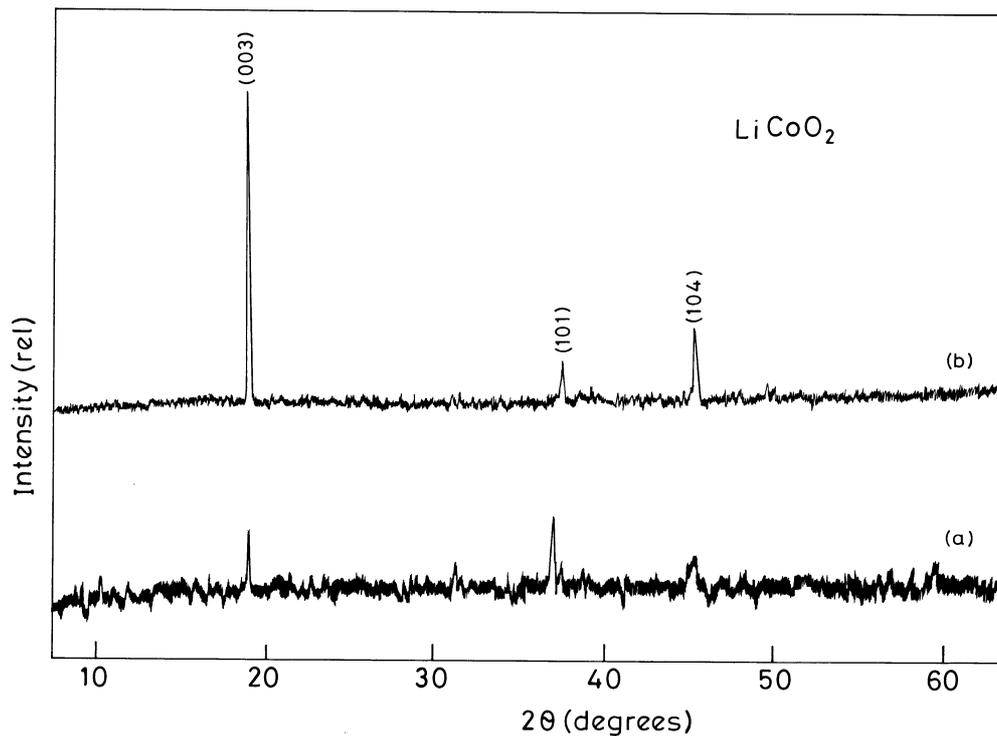


Figure 3. Powder X-ray diffraction pattern of layered LiCoO_2 prepared by (a) solution route and (b) solid state route.

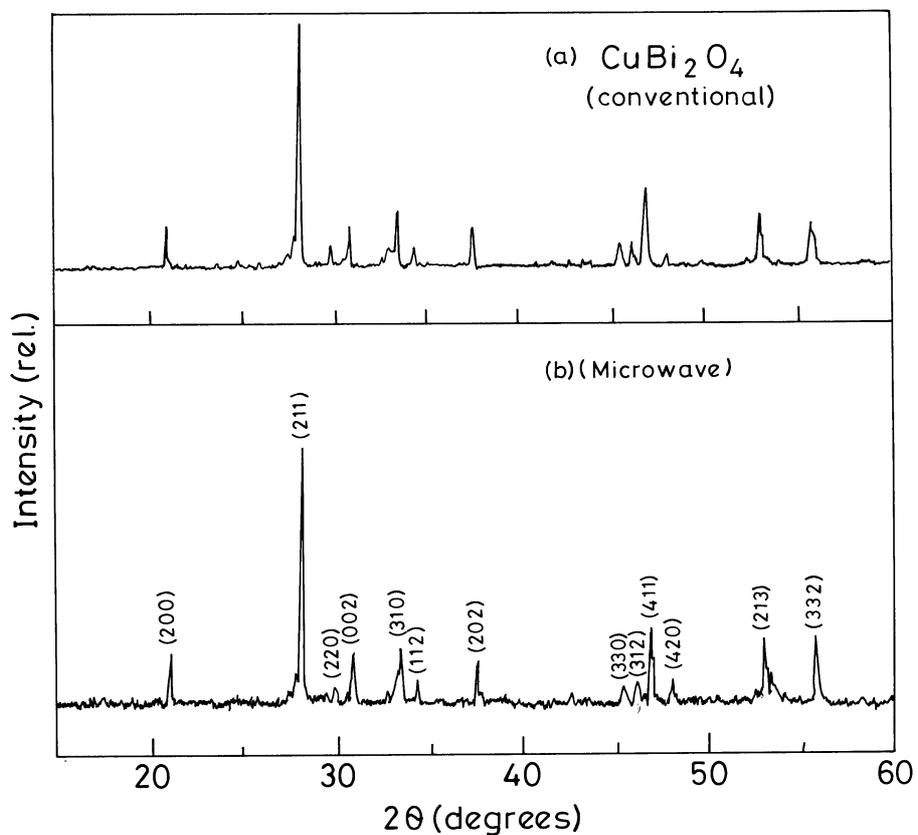


Figure 4. Powder X-ray diffraction pattern of CuBi_2O_4 prepared by (a) conventional and (b) microwave methods.

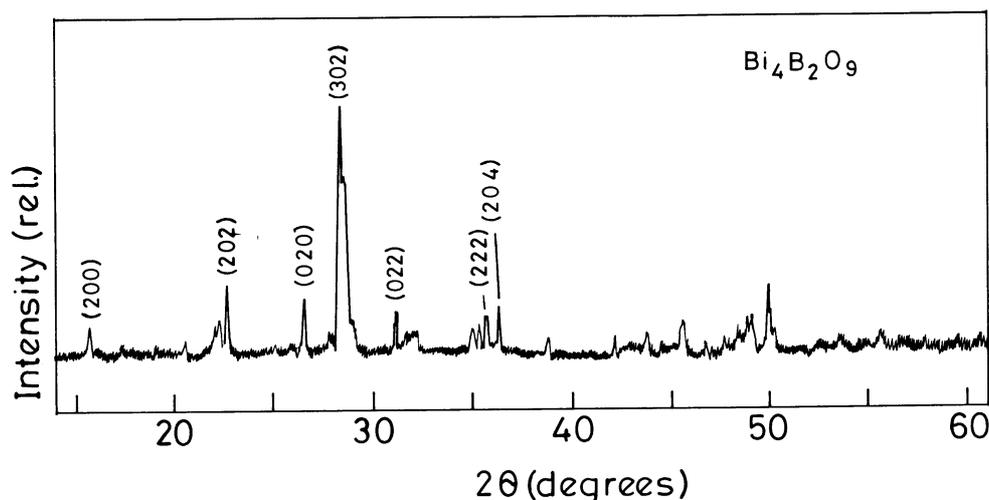


Figure 5. X-ray pattern of $\text{Bi}_4\text{B}_2\text{O}_9$ prepared by microwave route.

in amorphous carbon, which gave LiCoO_2 possessing very good crystallinity (figure 3b) within 5 min of irradiation in microwaves.

3.3 CuBi_2O_4

Microwave irradiation of a mixture of CuO and Bi_2O_3 for just 5 min yielded monophasic, tetragonal CuBi_2O_4 (figure 4a) with lattice parameters $a = 8.504 \text{ \AA}$ and $c = 5.811 \text{ \AA}$. These lattice parameter values are in good agreement with literature reports ($a = 8.510 \text{ \AA}$ and $c = 5.814 \text{ \AA}$) [JCPDS File no. 26-502]. Alternately, when a mixture of CuO and $(\text{BiO})_2\text{CO}_3$ was pelletized and embedded in amorphous carbon, the reaction was complete in under a minute. For purposes of comparison, CuBi_2O_4 was also prepared using the conventional procedure (Boivin *et al* 1973). In this procedure, the initial reactants (CuO and Bi_2O_3) are heated at 523 K for 2 h following which two additional heat treatments are given at 623 and 723 K for 6 h each. At every stage, the powders are ground repeatedly. Final heat treatment is given at 873 K for 4 h. XRD (figure 4b) of the material obtained by this method gave lattice parameters $a = 8.503 \text{ \AA}$ and $c = 5.817 \text{ \AA}$. The superiority of the microwave method, which gives the product in a single step irradiation and avoids the several steps involved in the conventional method, is self-evident. Also, the microwave method yields CuBi_2O_4 of better crystallinity as can be seen from the XRD patterns.

3.4 $\text{Bi}_4\text{B}_2\text{O}_9$

The compound $\text{Bi}_4\text{B}_2\text{O}_9$ was synthesized by a microwave method by grinding $(\text{BiO})_2\text{CO}_3$ and H_3BO_3 into a pellet, which was placed in amorphous carbon and irradiated

Table 1. Microwave prepared electrode materials and their preparative conditions.

Electrode No.	material	Reactants	Time (min)
1	LiMn_2O_4	$\text{Li}_2\text{CO}_3 + \text{MnO}_2^*$ $\text{LiI} + \text{MnO}_2$	5 6
2	CuBi_2O_4	$\text{CuO} + \text{Bi}_2\text{O}_3$ $\text{CuO} + (\text{BiO})_2\text{CO}_3^*$	5 1
3	LiCoO_2	$\text{LiOH} + \text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}^\#$ $\text{Li}_2\text{CO}_3 + \text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}^*$	10 5
4	$\text{Bi}_4\text{B}_2\text{O}_9$	$(\text{BiO})_2\text{CO}_3 + \text{H}_3\text{BO}_3$	1 (20% power) + 3 (100% power)

*indicates that reactants were pelletized and placed in amorphous carbon (secondary heater);

[#]indicates solution route using microwaves.

with microwaves. The initial heating was done at low power (20%) for about a minute for the removal of water and subsequently it was kept at high power for 3 min. The product was confirmed to be monophasic $\text{Bi}_4\text{B}_2\text{O}_9$ using X-ray diffraction (figure 5). In comparison, the conventional method (Levin and McDaniel 1962) is tedious and involves several intermittent grindings.

The various electrode materials prepared by the microwave route and their preparative conditions are summarized in table 1.

4. Conclusions

Electrode materials, which find potential applications in Li batteries, have been synthesized by a microwave route for the first time. The method should prove to be very attractive for large-scale production in view of the very short time involved for their synthesis.

Acknowledgement

Thanks are due to European Commission for the financial support through the project INCO-DC 950 400.

References

- Ahmad I, Dalton R C and Clark D E 1991 *J. Microwave Power & Electromagnetic Energy* **26** 128
- Baghurst D R and Mingos D M P 1988 *J. Chem. Soc., Chem. Commun.* 829
- Baghurst D R, Chippindale A M and Mingos D M P 1988 *Nature* **332** 311
- Barboux P, Tarascon J M and Shokoohi F K 1991 *J. Solid State Chem.* **94** 185
- Boivin M J C, Thomas D and Tridot G 1973 *Compt. Rend.* **C276** 1105
- Clark D E, Ahmad I and Dalton R C 1991 *Mater. Sci. Engg.* **A144** 91
- Dahn J R, von Sacken U and Michal C A 1990 *Solid State Ionics* **44** 87
- Dahn J R, von Sacken U, Juzkow M W and Janaby H A 1991 *J. Electrochem. Soc.* **138** 2207
- Fong R, Von Sacken U and Dahn J R 1990 *J. Electrochem. Soc.* **137** 2009
- Gummow R J, Thackery M M, David W I F and Hull S 1992 *Mater. Res. Bull.* **27** 327
- Guyomard D and Tarascon J M 1992 *J. Electrochem. Soc.* **139** 937
- Huang H and Bruce P G 1994 *J. Electrochem. Soc.* **141** L76
- Huang H and Bruce P G 1995 *J. Power Sources* **54** 52
- Jones S D and Akridge J R 1995 in *Handbook of solid state batteries and capacitors* (ed.) M Z A Munshi (Singapore: World Scientific) p. 209
- Kanno R, Takeda Y, Ichikawa T, Nakanashi K and Yamamoto O 1989 *J. Power Sources* **26** 535
- Kiggans J O, Hubbard C R, Steele R R, Kimrey H D, Holcombe C E and Tiegs T N 1991 *Ceram. Trans.* **21** 403
- Kladnig W F and Horn J E 1990 *Ceram. Int.* **16** 99
- Kniep R 1993 *Angew. Chem.* **32** 1411
- Landry C C and Barron A R 1993 *Science* **260** 1653
- Lazzari M and Scrosati B 1980 *J. Electrochem. Soc.* **127** 773
- Levin E M and McDaniel C L 1962 *J. Am. Ceram. Soc.* **45** 355
- Mingos D M P and Baghurst D R 1991 *Chem. Soc. Rev.* **20** 1
- Mingos D M P and Baghurst D R 1992 *Br. Ceram. Trans. J.* **91** 124
- Mizushima K, Jones P C, Wiseman P J and Goodenough J B 1980 *Mater. Res. Bull.* **15** 783
- Mohri M et al 1989 *J. Power Sources* **26** 545
- Murphy D W and Carides J N 1979 *J. Electrochem. Soc.* **126** 349
- Murphy D W, De Salvo F J, Carides J N and Waszczak J V 1978 *Mater. Res. Bull.* **13** 1395
- Nagaura T 1990 *Prog. Batt. Col. Cells* **9** 20
- Ozawa K 1994 *Solid State Ionics* **69** 212
- Peled E, Lombardi A and Schlaikjer C R 1983 *J. Electrochem. Soc.* **130** 1362
- Ramesh P D and Rao K J 1995 *Adv. Mater.* **7** 177
- Ramesh P D, Vaidhyanathan B, Ganguli M and Rao K J 1994 *J. Mater. Res.* **9** 3057
- Rao K J and Ramesh P D 1995 *Bull. Mater. Sci.* **18** 447
- Rao K J, Vaidhyanathan B, Ganguli M and Ramakrishnan P A 1999a *Chem. Mater.* **11** 882
- Rao K J, Ramakrishnan P A and Gadagkar R 1999b *J. Solid State Chem.* **148** 100
- Tarascon J M and Guyomard D 1991 *J. Electrochem. Soc.* **138** 2864
- Tarascon J M and Guyomard D 1993 *Electrochim. Acta* **38** 1221
- Thomas M G S R, Bruce P G and Goodenough J B 1985 *J. Electrochem. Soc.* **132** 1521
- Vaidhyanathan B and Rao K J 1997a *Chem. Mater.* **9** 1196
- Vaidhyanathan B and Rao K J 1997b *J. Mater. Res.* **12** 3225
- Vaidhyanathan B, Ganguli M and Rao K J 1994 *J. Solid State Chem.* **113** 448
- Vaidhyanathan B, Ganguli M and Rao K J 1995 *Mater. Res. Bull.* **30** 1173
- Vaidhyanathan B, Raizada P and Rao K J 1997 *J. Mater. Sci. Lett.* **16** 2022
- Vaidhyanathan B, Prem Kumar C and Rao K J 1998 *J. Phys. Chem. Solids* **59** 121
- Whittaker A G and Mingos D M P 1992 *J. Chem. Soc., Dalton Trans.* 2751