

Effect of particle size and lattice strain on Debye–Waller factors of Fe₃C nanoparticles

E PURUSHOTHAM* and N GOPI KRISHNA[†]

Department of Physics, SR Engineering College (Autonomous), Warangal 506 371, India

[†]Department of Physics, Kakatiya University, Warangal 506 009, India

MS received 13 February 2013; revised 30 May 2013

Abstract. Fe₃C nanoparticle powders have been prepared by a high energized ball mill. The resulting nanoparticle powders were characterized by X-ray diffraction (XRD) and scanning electron microscopy (SEM) measurements. The high-energy ball milling of Fe₃C after 10 h resulted in crystalline size of about 5 nm. The Debye temperature, mean-square amplitudes of vibration, Debye–Waller factor, lattice parameters, particle size, lattice strain and vacancy formation of energies of Fe₃C nanoparticles prepared by ball mill have been obtained from X-ray integrated intensities. The integrated intensities have been measured with a Philips CWU 3710 X-ray powder diffractometer fitted with a scintillation counter using filtered CuK α radiation at room temperature and have been corrected for thermal diffuse scattering. The X-ray Debye temperatures obtained in the present investigation has been used to estimate the vacancy formation energies for Fe₃C nanoparticles.

Keywords. Nanocrystalline Fe₃C ball milling; XRD; SEM; lattice parameters; particle size; lattice strain, Debye–Waller factor; vacancy formation energy.

1. Introduction

In recent years, synthesis of nanoparticles is a subject of intensive research, because of their basic scientific interest as well as for the technological importance. The nanoparticles exhibit very interesting properties like electrical, optical, magnetic, chemical, etc and which could not be achieved by their bulk nanoparticles (Colvin *et al* 1994). Nanomaterials may also be used in various technological applications like medical imaging, drug targeting, refrigeration system and other biological applications and catalysis (Kesavan *et al* 1999).

Recently, chemists, physicists and material scientists have shown great interest in the development of new methods for the synthesis of nanomaterials. These materials are important for further miniaturization of electric devices, nanofluids (Abid *et al* 2001) enhance efficiency of heat engines, as chemical catalysts (Eastman *et al* 2001; Darugar *et al* 2006) and lasing materials (Fujiwara *et al* 1999). Physical and chemical properties of these materials are highly size-dependent. Therefore, it is important to develop novel techniques for the synthesis of nanomaterials.

Metal carbides are generally referred to as refractory materials due to their high melting temperatures and high hardness and are being used as cutting tools, wear-resistance parts and surface coating. They deform

plastically in a manner similar to *fcc* metals and become relatively soft and ductile at high temperatures. Because of their high chemical stability, high Young's modulus at high temperatures, good thermal shock resistance and thermal conductivity, metal carbides are also being used as structural materials (Caer and Matteazzi 1991). Usually, metal carbides are prepared by conventional ceramic route, which requires a very high temperature as well as good vacuum condition or ultra pure inert gas atmosphere. However, nanocrystalline metal carbides with homogeneous composition can be prepared at room temperature by mechanical alloying (MA), the stoichiometric mixture of elemental powders under inert atmosphere.

Mechanical alloying process is a very useful solid-state technique for fabrication of nanocrystalline structure with improved properties (Tanaka 1992; Calka 1993; Suryanarayana 2001). If the Fe–C system is composed of a very fine microstructure, which can be synthesized by MA, it is possible to produce an advanced material with high hardness, wear resistance, toughness and good magnetic properties.

The formation of Fe₃C carbide and some hexagonal carbides (Caer and Matteazzi 1991; Nadutov *et al* 2000; Shabashov *et al* 2001), formation of Fe₃C only (Caer *et al* 1990a, b) and formation of Fe₃C carbide (Tokumitsu 1997; Tokumitsu and Memoto 2001) have been reported earlier. For the mixtures with $x = 20$ –25%, in all the above cases, Fe₃C phase was obtained after a long period of milling with significant amount of Fe as an un-reacted powder and in none of the cases microstructures of the ball-milled samples

*Author for correspondence (psm45456@gmail.com)

were characterized in terms of lattice strain imperfections related to physical properties of the prepared materials.

The objectives of the present work are: (i) to produce nanocrystalline Fe_3C by high-energy ball milling of Fe and C (graphite) powders at room temperature and (ii) to calculate particle size, effect of lattice strain on the Debye–Waller factor. Ball-milled samples are related to several microstructure parameters like change in particle size, lattice strain and the effect of lattice strain on the Debye–Waller factor. All these microstructure parameters can be estimated quantitatively by analysing XRD patterns of ball-milled samples employing either of the Hall–Williamson’s method, as the XRD pattern of Fe_3C phase (orthorhombic) is composed of several overlapping reflections.

TEM is one of the powerful techniques for crystallite size measurement, but it has certain limitations. Since TEM images represent only a local region, many samples and images are required to provide average information for the entire sample. Not only this, the TEM sample preparation method is an involved and time consuming one. XRD technique is free from these limitations. X-ray diffraction is, on the other hand, a simple and easier approach for determination of crystallite size of powder samples.

The Debye–Waller factor is an important lattice dynamical property. There is considerable X-ray work on the Debye–Waller factors of Fe_3C . But it is interesting to study the effect of particle size and lattice strains on the Debye–Waller factors of these metals. Pradhan *et al* (2009) studied the microstructure characterization of nanocrystalline Fe_3C synthesized by high-energy ball-milling. Glushenkov *et al* (2008) showed reactive ball-milling to produce nanocrystalline ZnO. Inagaki *et al* (1971, 1973) showed that in several non-metallic powders, the strains produced during grinding have a significant effect on the Debye–Waller factors measured from X-ray diffraction intensities. Sirdeshmukh *et al* (1993) observed the effect of lattice strains on the Debye–Waller factors in semiconductor powder materials. Gopi Krishna and Sirdeshmukh (1993) studied the effect of lattice strains on the Debye–Waller factor of ytterbium metal. Gopi Krishna *et al* (2010) studied the effect of lattice strains on the Debye–Waller factor of Mg, Zn and Cd for slow grinding in an agate mortar. In the present investigation, results of a systematic study of the lattice parameters, effect of particle size and lattice strains on the Debye–Waller factors of Fe_3C metal powder is reported using ball mill. These results are being reported for the first time.

2. Experimental

Experimental profiles of un-milled and all ball-milled powders are, therefore, fitted with the simulated powder diffraction patterns generated considering the contribution from the following three phases: (i) α -Fe (cubic, space group: $Im3m$, $a = 0.2866$ nm), (ii) graphite[®] (hex,

$a = 0.2740$ nm, $c = 0.6707$ nm, space group: $P63/mmc$) and (iii) Fe_3C (orthorhombic, space group: $Pnma$, $a = 0.5091$ nm, $b = 0.6743$ nm, $c = 0.4526$ nm). Highly pure α -Fe and graphite rods obtained from the Solid State Physics Laboratory, New Delhi, were used. The powder samples were obtained by gently filing highly pure Fe and graphite rods with a jeweller’s file and mixed in 3:1 molar ratio of Fe and C. A part of this powder was used to prepare the initial sample. The remaining powder was subjected to milling in a high-energy planetary ball mill (Model: Retsch, PM 100, Germany) for 2, 4, 6, 8 and 10 h to produce strains and decrease the particle size in a stainless steel chamber using tungsten carbide and zirconia balls of 10 mm ϕ and 3 mm ϕ ball sizes, respectively.

The un-milled sample (0 h) is fitted very well with Fe but with preferred orientation of graphite particles along [0 0 2]. Graphite reflections disappear within 30 min of milling and peak-broadening of Fe reflections increases continuously with increasing milling time up to 2 h of milling. This peak-broadening is fitted by considering both the effects of small particle size and lattice strain, which are reasoned due to cold working on Fe lattice during ball-milling.

X-ray diffractograms were recorded with the initial sample and with samples prepared after each spell of milling. The diffractograms were obtained with a Philips CWU 3710 X-ray powder diffractometer in the 2θ range of 20–120° using filtered $\text{CuK}\alpha$, a goniometer speed of 0.5° per min and a chart speed of 20 mm/min. XRD patterns of Fe_3C are given in figure 1. All measurements were made at room temperature. The observed integrated intensities have been corrected for thermal diffuse scattering using the method of Chipman and Paskin (1959).

3. Method of analysis

The procedure for the determination of directional mean-square amplitudes of vibration $\langle u_{\parallel}^2 \rangle$ and $\langle u_{\perp}^2 \rangle$ from the

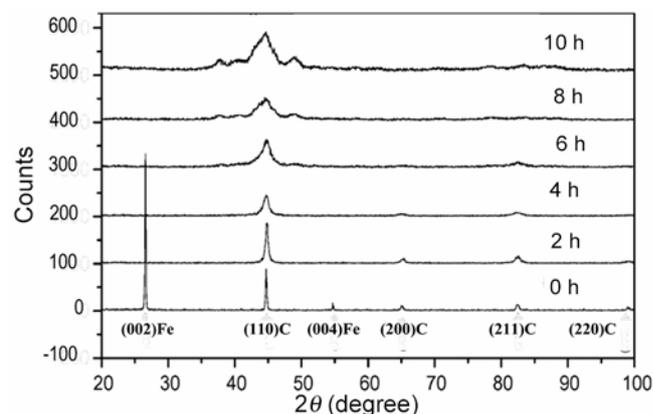


Figure 1. X-ray powder diffraction patterns of Fe_3C .

intensity data and the estimation of associated errors is as discussed by Gopi Krishna *et al* (1986). The average mean square amplitude $\langle u_{av}^2 \rangle$ can be obtained from the relation:

$$\langle u_{av}^2 \rangle = 1/3(\langle u_{\parallel}^2 \rangle + 2\langle u_{\perp}^2 \rangle), \quad (1)$$

and the directional Debye–Waller factors B_{\perp} and B_{\parallel} were obtained from the equations

$$\left. \begin{aligned} B_{\perp} &= 8\pi^2 \langle u_{\perp}^2 \rangle \\ B_{\parallel} &= 8\pi^2 \langle u_{\parallel}^2 \rangle \end{aligned} \right\}. \quad (2)$$

The mean Debye–Waller factor B is given by

$$B = (2B_{\perp} + B_{\parallel})/3.$$

The directional Debye temperatures θ_{\perp} , θ_{\parallel} and mean Debye temperature θ_M were obtained from B_{\perp} , B_{\parallel} and B , respectively using the Debye–Waller theory (James 1967) relation:

$$\left. \begin{aligned} B &= (6h^2/Mk_B\theta_M)W(X) \\ B_{\perp} &= (6h^2/Mk_B\theta_{\perp})W(X) \\ B_{\parallel} &= (6h^2/Mk_B\theta_{\parallel})W(X) \end{aligned} \right\}, \quad (3)$$

where h is the Planck's constant, k_B the Boltzmann constant, M the atomic weight. The function $W(X)$ is given by:

$$W(X) = [\phi(X)/X + (1/4)], \quad (4)$$

where $X = \theta_M/T$, T is the temperature of the crystal and $\phi(X)$ the Debye function. The values of $W(X)$ for a wide range of X can be obtained from the International Standard tables (1968).

3.1 Lattice strain and particle size determination

When the size of the individual crystals is less than about 100 nm, the term 'particle size' is usually used. When the crystallites of a material are smaller than 100 nm, they have a number of too small parallel diffraction planes and so they produce broadened diffraction peaks instead of a sharp peak. Lattice strain present in the sample is another cause of broadening of Bragg diffraction peaks. In addition to this, there are instrumental factors such as unresolved α_1 and α_2 peaks, imperfect focusing which lead to the line broadening. There are various methods in practice to estimate the particle size. X-ray diffraction is a simpler and easier approach for the determination of precise particle size and the lattice strain in powder samples. The principle involved in the X-ray diffraction approach is precise quantification of the broadening of the Bragg diffraction peaks. Scherrer equation, Hall–Williamson method and Warren–Averbach method are some of the techniques based on this principle. Of the above methods, Scherrer equation method for the estimation of particle size does not take into account the broadening due to lattice strain present in the sample. As such

in the present investigation, the lattice strains have been estimated using Hall–Williamson method. Recently, Bharati *et al* (2006) used this method to estimate the lattice strain and particle sizes of silver nanoparticles and composite silver nanoparticles. In this method, the integral breadth of the diffraction peak is determined. The integral breadth is given by the integrated intensity divided by the maximum intensity. Thus, the observed peak broadening, B_o may be represented as:

$$B_o = B_i + B_r, \quad (5)$$

where B_o is the observed peak broadening in radians, B_i the instrumental broadening in radians and B_r the broadening due to the small particle size and lattice strain. The instrumental broadening has been estimated using a pure strain-free fine sodium chloride powder sample subjected to XRD under identical conditions as those for the strained metallic powders. Equation (5) holds good if the diffraction peaks exhibit purely Cauchy profile. However, when the diffraction peaks are partly Cauchy and partly Gaussian for profiles, the following relation between B_o , B_i and B_r holds good (Bharati *et al* 2006)

$$B_r = [(B_o - B_i)(B_o^2 - B_i^2)^{1/2}]^{1/2}. \quad (6)$$

Now, according to Scherrer equation, the broadening due to small particle size may be expressed as

$$B_c = \frac{k\lambda}{t} \cos\theta, \quad (7)$$

where B_c is the broadening solely due to small crystallite size, K a constant whose value depends on particle shape and usually taken as unity, t the crystallite size in nanometers, θ the Bragg angle and λ the wavelength of incident X-ray beam in nanometers.

Similarly, according to Wilson (1949), the broadening due to lattice strain may be expressed by the relation:

$$B_s = \varepsilon \tan\theta, \quad (8)$$

where B_s is the peak broadening due to lattice strain, ε the strain distribution within the material and θ the Bragg

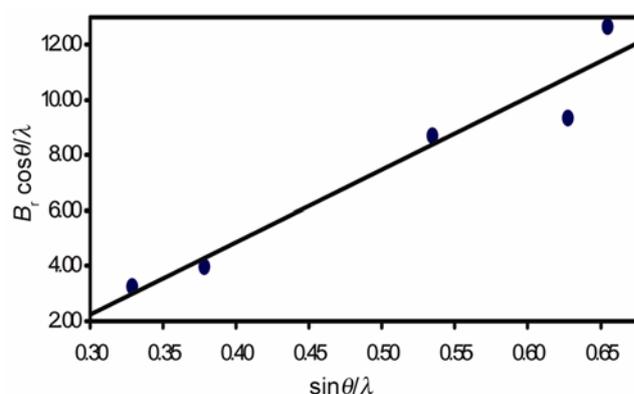
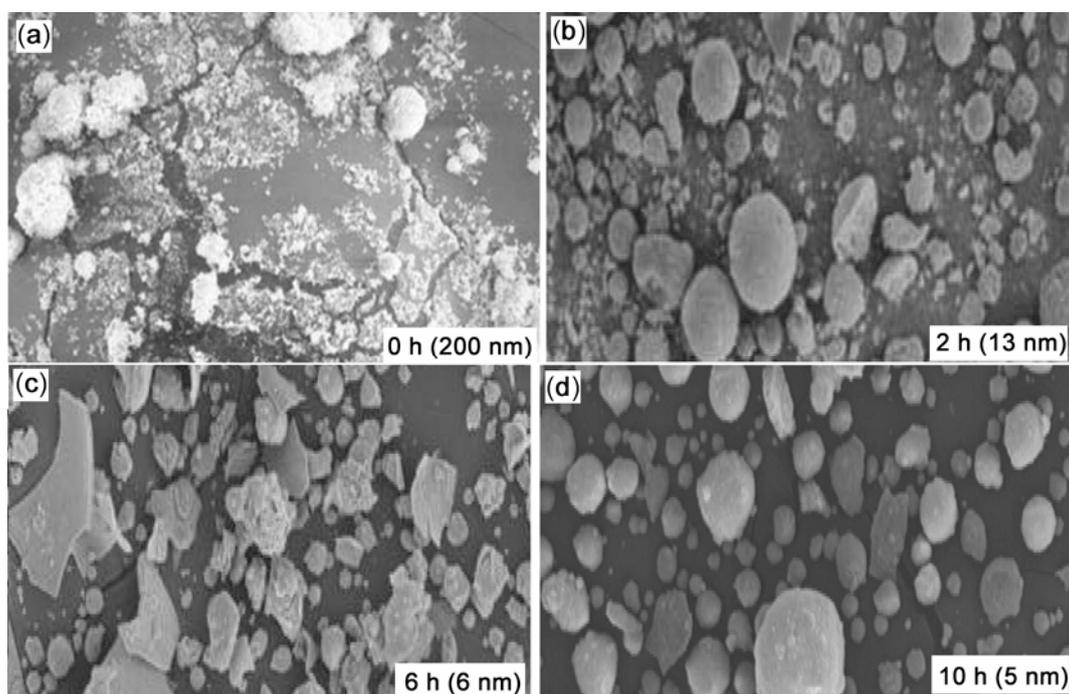


Figure 2. Plot of $B_i \cos\theta/\lambda$ vs $\sin\theta/\lambda$ for Fe₃C after milling for 8 h.

Table 1. Values of particle size (t), lattice strain (ε), mean Debye–Waller factor (B), root mean square amplitudes of vibration ($\langle u \rangle$), mean Debye temperature (θ_M) and energy of vacancy formation (E_f) of strained nano Fe₃C powder.

Metal	Milling time (h)	$\varepsilon \times 10^3$	t (nm)	a (nm)	b (nm)	c (nm)	$\langle u \rangle$	B (Å ²)	θ_M (K)	E_f (eV)
α -Fe	0	0.8225	139.23	0.2866	–	–	–	0.36	428	–
C	0	0.9903	192.28	0.2740	–	0.6707	–	–	–	–
Fe ₃ C	0	1.1526	198.67	0.5091	0.6743	0.4526	0.0063	0.30	274	5.86
Fe ₃ C	2	3.4129	11.12	0.5078	0.6792	0.4532	0.0076	0.46	223	3.74
Fe ₃ C	4	6.6233	5.36	0.5080	0.6785	0.4515	0.0083	0.69	182	2.65
Fe ₃ C	6	8.9521	4.56	0.5096	0.6784	0.4521	0.0098	0.93	163	1.89
Fe ₃ C	8	10.0433	4.49	0.5077	0.6794	0.4521	0.0147	1.05	149	1.46
Fe ₃ C	10	11.7536	4.49	0.5076	0.6795	0.4521	0.0241	1.22	128	0.82

**Figure 3.** (a–d) Scanning electron microscopy (SEM) morphology of powder particles (a) 0 h, (b) after 2 h, (c) after 6 h and (d) after 10 h, of milling of Fe₃C nanoparticle powders.

angle. Based on (7) and (8), the total peak broadening, B_r may be expressed as:

$$B_r = \frac{k\lambda}{t \cos \theta} + \varepsilon \tan \theta, \quad (9)$$

which can be written as

$$B_r \cos \theta = \frac{k\lambda}{t} + \varepsilon \sin \theta. \quad (10)$$

The plot of $B_r \cos \theta / \lambda$ vs $\sin \theta / \lambda$ is a straight line with slope equal to ε and hence the particle size t can be estimated from the intercept. Typical Hall–Williamson plot between $B_r \cos \theta / \lambda$ and $\sin \theta / \lambda$ is shown in figure 2.

The lattice strains were determined from the plot of $B_r \cos \theta / \lambda$ against $\sin \theta / \lambda$ following standard procedures (Kaelble 1967). The measured half-widths were corrected

for instrumental broadening with reference to a pure strain-free silicon powder. The variation of particle size with milling time is within the limits of experimental errors. This shows that while the milling is enough to create strains, it affects the particle size to a measurable extent. A typical Hall–Williamson plot is shown in figure 2 for Fe₃C after milling for 8 h.

4. Results and discussion

Figure 1 shows XRD patterns of the (0 h) mixture (3:1 mol) of α -Fe and graphite powders ball milled at room temperature for different durations 0, 2, 4, 6, 8 and 10 h. The values of the lattice parameters, particle size, lattice strain, root mean square amplitudes of vibration, Debye–Waller factors and Debye temperatures of Fe₃C

powders, ground for different durations, obtained in the present study are given in table 1. Figure 2 shows plot of $B_r \cos \theta / \lambda$ vs $\sin \theta / \lambda$ for Fe₃C after milling for 8 h. Figure 3(a–d) shows the scanning electron microscopy (SEM) morphology of powder particles: (a) 0 h (200 nm), (b) after 2 h (13 nm), (c) after 6 h (6 nm) and (d) after 10 h (5 nm) of milling of Fe₃C nanoparticle powders. SEM pictures are good evidence for nanocrystalline state of Fe₃C nanoparticles by showing agglomerated spherical particles of irregular-shape particles.

Figure 4 shows variation in lattice parameter which indicates that at the early stage of milling, carbon atoms could not be entered into the α -Fe matrix and thin graphite layers began to distribute around the α -Fe grain boundaries. After 1 h of milling, carbon atoms started to diffuse through the boundaries of nano α -Fe grain and an interstitial Fe–C solid solution is formed with a trace amount of carbon. The orthorhombic Fe₃C phase is formed after 2 h of milling with lattice parameters very close to the reported value and remains stable up to 8 h of milling with insignificant changes in lattice parameters are given in table 1, this is similar to the observations of Pradhan *et al* (2009).

Although, values of Debye–Waller factor, amplitude of vibration and Debye temperature in the a and c directions

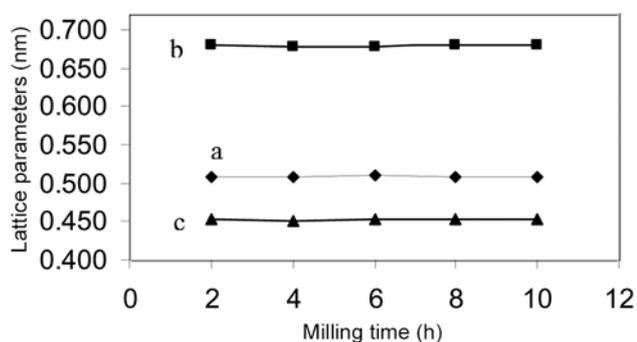


Figure 4. Variation of lattice parameters of Fe₃C phases in ball-milled mixture of α -Fe and graphite (3:1 mol) with increasing milling time.

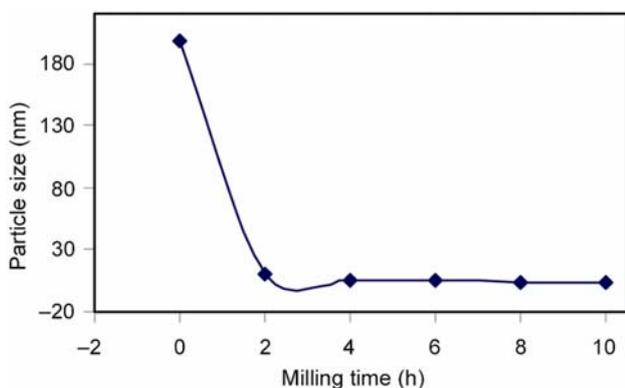


Figure 5. Variation of particle size (t) of Fe₃C with increasing milling time.

have been determined separately, the average values of these quantities are given in table 1. The objective of the present work is to investigate the strain dependence of Debye–Waller factors.

Figure 5 shows variation of the particle size (t) for different milling times for Fe₃C, particle size decreases with milling time. Figures 6 and 7 show variation of the lattice strain (ϵ) and Debye–Waller factor (B) for different milling times for Fe₃C. Both lattice strain and Debye–Waller factor increase with milling time. This is similar to the observations of Inagaki *et al* (1971, 1973), Sirdeshmukh *et al* (1993), Gopi Krishna and Sirdeshmukh (1993), Gopi Krishna *et al* (2010). In the present work, the Debye–Waller factor increases with milling time and lattice strain in a slightly nonlinear fashion.

Figure 8 shows variation between lattice strain (ϵ) and Debye–Waller factor (B). An extrapolation of the B vs ϵ curve to $\epsilon = 0$ gives the value of Debye–Waller factors of 0.24 Å² for Fe₃C. The zero-strain value of Debye–Waller factor is less than the value for the initial sample. Thus, the Debye–Waller factor of Fe₃C powder sample carries an effect due to lattice strain. While comparing the Debye–Waller factors calculated from the lattice dynamical models with experimental results, Vetelino *et al* (1972) attributed the difference to inaccuracies in the experimental values caused by neglecting the TDS corrections. The repeated milling of the powder sample leads to lattice distortion which gives rise to microstrains

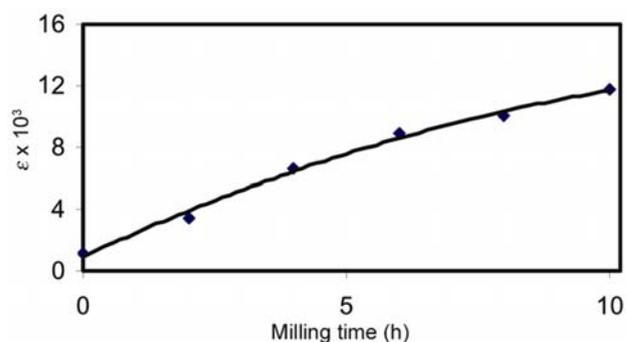


Figure 6. Variation of particle size (t) of Fe₃C with increasing milling time.

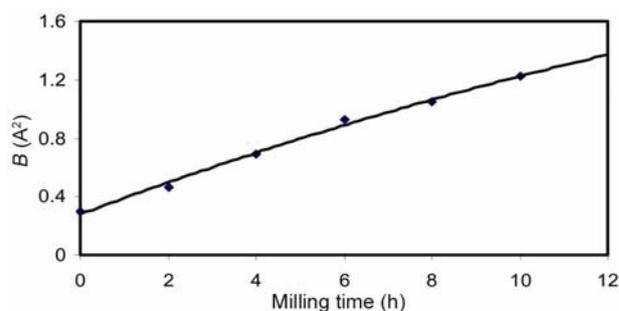


Figure 7. Variation of Debye–Waller factor (B) of Fe₃C with increasing milling time.

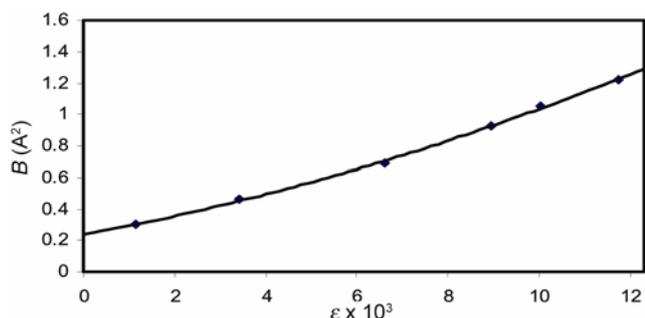


Figure 8. Variation of Debye–Waller factor (B) of Fe_3C with lattice strain.

in the lattice. These microstrains increase the contribution of static component of Debye–Waller factor. Thus, both lattice strain and observed Debye–Waller factor, which is the sum of static and thermal components, increase with milling time. Thus, whenever Debye–Waller factors are determined from X-ray intensities on powder samples, it is desirable to make an estimate of the lattice strain and if the strain is large, a suitable correction is to be made as in the present study. The Debye temperatures derived from the zero strain values of Debye–Waller factor of Fe_3C is 289 K.

Glyde (1967) derived the following relation between the energy of vacancy formation (E_f) and the Debye temperature (θ) of a solid:

$$E_f = A(k/h)^2 M \theta^2 a^2, \quad (11)$$

where a is the interatomic spacing, A a constant shown to be equal to 1.17×10^{-2} , M the molecular weight and h and k are the Planck's and the Boltzmann's constants, respectively. Glyde recommended the use of X-ray based values in (11). The validity of (11) was verified for a number of *fcc*, *bcc* and *hcp* metals (micro- and macro-properties of solids, 2006). Therefore, the X-ray Debye temperatures obtained in the present work have been used to study the variation of vacancy formation energy as a function of lattice strain in Fe_3C . The values of vacancy formation energies are also included in table 1.

5. Conclusions

Fe_3C powder was strained by milling for 10 h. From a study of X-ray diffractograms recorded at different stages of milling, it is observed that milling for 10 h has systematic effect on the particle size. However, the milling produces lattice strain and also enhances the effective Debye–Waller factor. By an extrapolation of the plot between the Debye–Waller factor and the lattice strain, the zero strain Debye–Waller factors are obtained for Fe_3C . The variation of vacancy formation energy as a function of lattice strain has been studied.

References

- Abid J P, Girault H H and Brevet P F 2001 *Chem. Commun.* 829
- Bharati R, Rehani P, Joshi B, Kirit N Lad and Arun Pratap 2006 *Indian J. Pure Appl. Phys.* **44** 157
- Caer G Le, Bauer-Grosse E, Pianelli A, Bouzy E and Matteazzi P 1990a *J. Mater. Sci.* **25** 4726
- Caer G Le, Matteazzi P, Bauer-Grosse E, Pultz B and Pianelli A 1990b *Colloque de Phys. Colloque* **51** (suppl. C4) c4
- Caer G Le and Matteazzi P 1991 *Hyperfine Interact.* **66** 309
- Calka A 1993 *Key Eng.* **81–83** 17
- Chipman D R and Paskin A 1959 *J. Appl. Phys.* **30** 1938
- Colvin V L, Schlamp M C and Alivisatos A P 1994 *Nature* **370** 354
- Darugar Q, Qian W and El-Sayed M A 2006 *J. Phys. Chem.* **B110** 143
- Eastman J A, Cnoi U S, Li S, Yu W and Thompson L J 2001 *Appl. Phys. Lett.* **78** 718
- Fujiwara H, Yanagida S and Kamat P V 1999 *J. Phys. Chem.* **B103** 2589
- Glushenkov A M, Zhang H Z and Chen Y 2008 *Mater. Lett.* **62** 4047
- Glyde H R 1967 *J. Phys. Chem. Solids (GB)* **28** 2061
- Gopi Krishna N and Sirdeshmukh D B 1993 *Indian J. Pure Appl. Phys.* **31** 198
- Gopi Krishna N et al 2010 *Indian J. Phys.* **84** 887
- Gopi Krishna N, Sirdeshmukh D B, Rama Rao B, Beandry B J and Gschneidner Jr K A 1986 *Indian J. Pure Appl. Phys.* **24** 324
- Inagaki M et al 1971 *J. Mater. Sci.* **6** 1520
- Inagaki M, Furuhashi H, Ozeki T and Naka S 1973 *J. Mater. Sci.* **8** 312
- International tables for X-ray crystallography 1968 (Birmingham: Kynoch Press) Vol. III
- James R W 1967 *The optical principles of the diffraction of X-rays* (London: Bell and Sons)
- Kaelble E F 1967 *Handbook of X-rays* (New York: McGraw Hill)
- Kesavan V, Sivanand S P, Chandrasekaran S, Kolytipin Y and Gedanken A 1999 *Angew. Chem. Int. Ed.* **38** 3521
- Micro- and Macro-Properties of Solids 2006 Springer Series in Material Science
- Nadutov V M, Garamus V M and Rawers J C 2000 *Mater. Sci. Forum* **721** 343
- Pradhan S K et al 2009 *B. J. Alloys Comp.* **477** 127
- Shabashov V A, Mukosccc A G and Sagaradze V V 2001 *Mater. Sci. Eng.* **A307** 91
- Sirdeshmukh D B, Subhadra K G, Hussain K A, Gopi Krishna N and Raghavendra Rao B 1993 *Cryst. Res. Technol.* **28** 15
- Suryanarayana C 2001 *Prog. Mater. Sci.* **46** 1
- Tanaka T, Ishihara K N and Shingu P H 1992 *Met. Trans.* **23A** 2431
- Tokumitsu K 1997 *Mater. Sci. Forum* **127** 235
- Tokumitsu K and Memoto M U 2001 *Mater. Sci. Forum* **183** 360
- Vetelino J F, Gaur S P and Mitra S S 1972 *Phys. Rev.* **B5** 2360
- Wilson A J C 1949 *X-ray optics* (London: Methuen)