

Capped semiconductor colloids: Synthesis and photochemistry of CdS capped SnO₂ nanocrystallites

ROBERT KENNEDY^a, IGNACIO MARTINI^a,
GREG HARTLAND^a and PRASHANT V KAMAT^{b*}

^aDepartment of Chemistry, University of Notre Dame, Notre Dame, IN 46556, USA

^bRadiation Laboratory, University of Notre Dame, Notre Dame, IN 46556, USA

e-mail: Hartland.1@nd.edu

e-mail: Kamat.1@nd.edu

Abstract. CdS-capped SnO₂ (CdS@SnO₂) and SiO₂ (CdS@SiO₂) colloids of 50–80 Å in diameter have been prepared in aqueous medium. Significant quenching of CdS emission is observed in the CdS@SnO₂ system as the electrons are injected from the excited CdS shell into the SnO₂ core. Photoinduced charge separation in this system also results in transient bleaching in the 450 nm region. Picosecond laser flash photolysis studies of composite semiconductor nanoclusters that highlight the effect of the metal oxide core on the photophysical properties of the outer CdS shell are described.

Keywords. CdS-capped SnO₂ and SiO₂ colloids; composite semiconductor systems; emission properties; molecular devices.


1. Introduction

Recently, considerable interest is focused on developing composite semiconductor materials with coupled capped geometries^{1,2}. This approach is based on the principle of combining two semiconductors with different energy levels^{3,4}. The charge separation that can be achieved with composite semiconductor systems makes these systems attractive for designing molecular devices and integrated chemical systems for solar energy conversion. For example, coupled semiconductor particles have been shown to improve the photocurrent generation in thin particle films of TiO₂-CdS^{5–8}, ZnO-CdS⁹ and TiO₂/CdSe^{10,11}. Such coupled semiconductor thin films not only extend the photoresponse of large bandgap semiconductors but also rectify the flow of photo-generated charge carriers¹⁰ and improve the efficiency of dye sensitization¹². Composite semiconductor systems such as TiO₂/CdS, TiO₂/SnO₂, TiO₂/WO₃, TiO₂/MnO₂, TiO₂/SiO₂, TiO₂/ZrO₂ and TiO₂/WO₃ have also been beneficial in enhancing the rates of photocatalytic degradation processes^{13–21}.

The capped nanoclusters essentially have a core-shell geometry, while in coupled systems the two semiconductor nanoclusters are in contact with each other. The principle of charge separation in capped and coupled semiconductor systems is illustrated in scheme 1. While the mechanism of charge separation in a capped semiconductor system is similar to that in a coupled semiconductor system, the interfacial charge transfer or charge collection at this multicomponent semiconductor

*For correspondence

Contribution No. 3961 from the Notre Dame Radiation Laboratory, USA

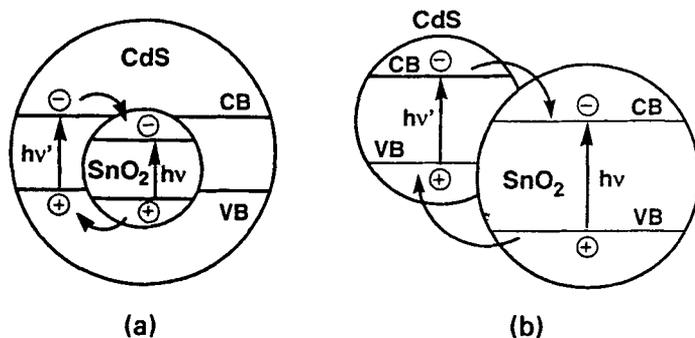

Scheme 1 Principle of charge separation in semiconductor heterostructures: (a) Capped (or core-shell) geometry and (b) Coupled geometry. Electrons accumulate at the conduction band (CB) of SnO_2 while holes at the valence band (VB) of CdS.

system is significantly different. Only one of the charge carriers is accessible at the surface in a capped semiconductor system, thus making selective charge transfer possible at the semiconductor/electrolyte interface. The other charge carrier (e.g., the electron of Scheme 1) gets trapped within the inner semiconductor particle and is not readily accessible. In a coupled semiconductor system both holes and electrons are accessible for selective oxidation and reduction processes on different particle surfaces.

The photophysical and photochemical properties of a variety of coupled and capped type semiconductor nanoclusters have been investigated in several laboratories. These systems include CdS-TiO_2 ^{22,23}, CdS-PbS ²⁴, CdS-ZnO ^{9,22}, CdS-AgI ²³, $\text{Cd}_3\text{P}_2\text{-TiO}_2$ and $\text{Cd}_3\text{P}_2\text{-ZnO}$ ²⁵, ZnO-ZnS ²⁶, ZnO-ZnSe ²⁷, $\text{AgI-Ag}_2\text{S}$ ²⁸, $\text{SnO}_2\text{-TiO}_2$ ²⁹ and CdS/HgS ^{30,31}. In our earlier studies, we have shown that excitation of CdS colloids coupled with a metal oxide colloids such as ZnO ⁹ or TiO_2 ²³ results in the injection of electrons into the lower lying conduction band of the metal oxide. The charge injection process in these systems was shown to occur within the pulse duration of 20 ps. Recent studies have indicated that such an inter-particle electron transfer occurs within 500 fs–2 ps^{32,33}.

Brus and his coworkers have demonstrated the feasibility of controlling the nucleation and growth of CdSe on ZnS and ZnS on CdSe quantum crystallites³⁴. Recently, Eychmüller and his coworkers^{30,35} have demonstrated interesting fluorescence properties of CdS colloids capped with HgS. Elucidation of the energetic structure and charge carrier dynamics of this system led to the conclusion that its electronic properties are significantly different from the sum of the separate particles. Optical properties of PbS coated CdS particles have also been investigated^{36,37}. Development of such semiconductors is interesting, since by changing the thickness of the shell and the particle radius, the overlap of the wavefunctions and bandgap can be altered. Theoretical models for the quantum confinement in semiconductor heterostructures have been developed by Haus and coworkers³⁸.

In view of the many interesting features of this core-shell type semiconductor system we have synthesized CdS capped SnO_2 colloids for investigating photoinduced charge transfer processes. In the present paper, our initial studies describing the preparation and photophysical properties are presented.

2. Experimental

2.1 Materials

SnO₂ colloidal suspension in water (18%, particle size 30–50 Å) was obtained from Alfa Chemicals and used without further purification. Colloidal silica (# 2326, 14.5%, 50 Å, pH 9.0) was a gift sample from NALCO. All other chemicals were analytical reagents and used as supplied. Absorption spectra were recorded with a Perkin Elmer 3840 Diode Array Spectrophotometer. Emission spectra were recorded with SLM 8000 spectrofluorometer.

2.2 TEM measurements

A small drop of the colloidal suspension was applied to carbon-coated copper grids before using them for transmission electron microscopic examination. Particle sizes were determined from the photographs taken at a magnification of 200000–300000X using a Hitachi H600 transmission electron microscope. The pictures were further magnified by photographic enlargement.

2.3 Picosecond laser flash photolysis

Picosecond laser flash photolysis experiments were performed with 355 nm laser pulses from a mode-locked, Q-switched Continuum YG-501 DP Nd:YAG laser system (output 2–3 mJ/pulse, ~ 18ps pulse width). The white light continuum picosecond probe pulse was generated by passing the fundamental output through a D₂O/H₂O solution. The output was fed to a spectrograph (HR-320, ISDA Instruments, Inc.) with fiber optic cables and was analyzed with a dual diode array detector (Princeton Instruments, Inc.) interfaced with an IBM-AT computer. The details of the experimental setup and its operation are described elsewhere^{39,40}. Time zero in these experiments corresponds to the end of the excitation pulse.

3 Results and discussion

3.1 Synthesis of CdS capped SnO₂ colloids

The method employed in the preparation of capped colloids involves adsorption of Cd²⁺ ions on to the inner core semiconductor colloid followed by the exposure of the solution to H₂S. A typical procedure involves addition of 0.1 ml of 0.1 M Cd(ClO₄)₂ to a 25 ml aqueous suspension of 0.04% SiO₂ or SnO₂ colloids (pH ~ 10) in an airtight glass vessel. The suspension in the glass vessel was cooled to ~ 273 K and was then subjected to vacuum for a brief period of time to remove dissolved air. 25 ml of H₂S was then injected into the vessel. The solution slowly turned yellow as CdS precipitated on to the SiO₂ or SnO₂ core. After waiting for 2 min the excess H₂S was pumped off by subjecting the glass vessel to vacuum. The suspension was stable for several days. By controlling the concentration of Cd²⁺ it is possible to vary the thickness of the CdS shell. These capped colloids will be referred as SnO₂@CdS and SiO₂@CdS respectively in the following discussion.

3.2 Characterization of capped colloids

a. *Absorption spectra.* The absorption spectra of aqueous suspensions of capped colloids are compared with those of native colloids in figures 1A and B. The CdS

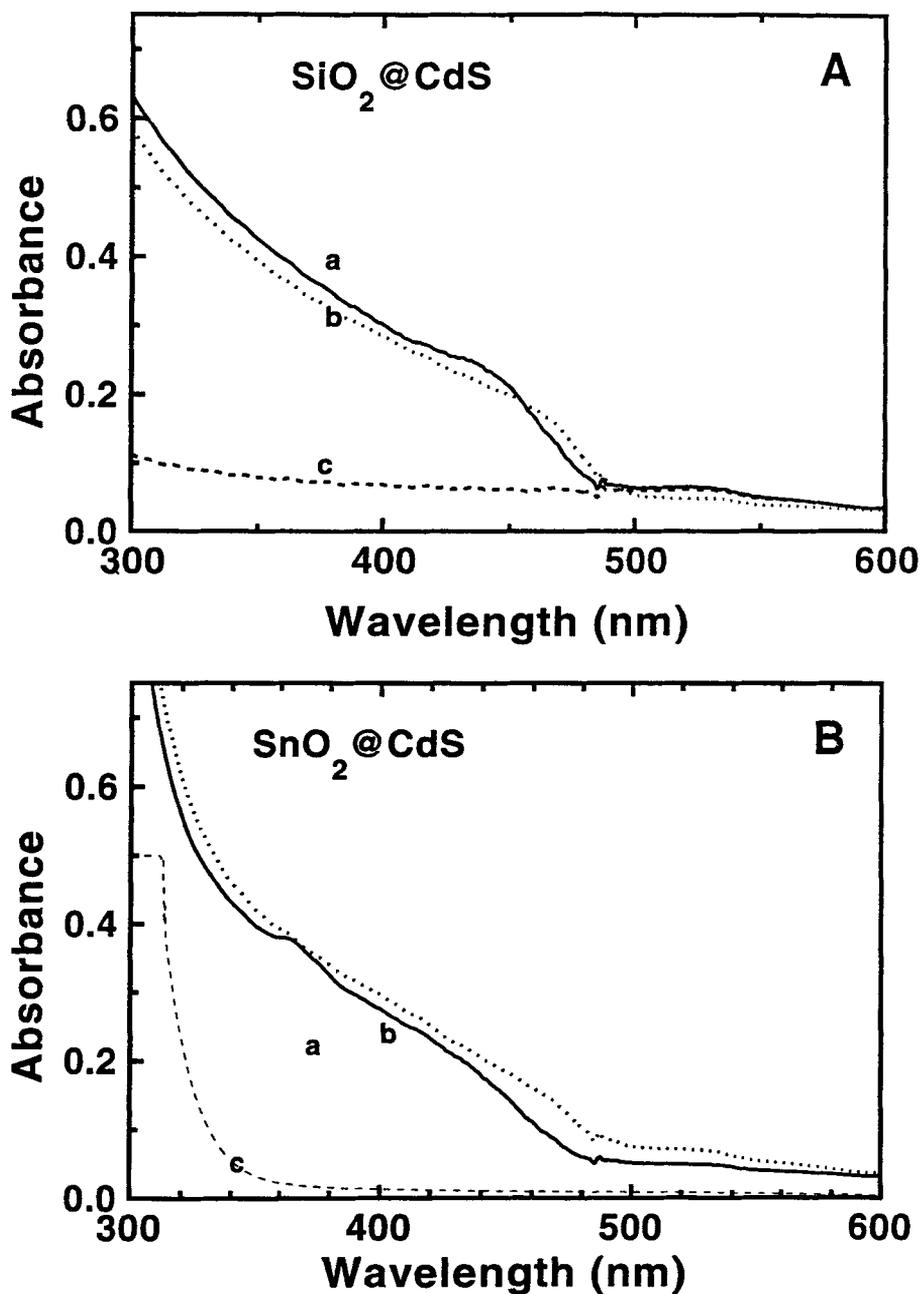


Figure 1. A. Absorption spectra of aqueous suspensions of SiO₂@CdS colloids (a) immediately after preparation and (b) after 3 days of aging. The spectrum of blank SiO₂ colloidal suspension is also shown (spectrum c).

B. Absorption spectra of aqueous suspensions of SnO₂@CdS colloids (a) immediately after preparation and (b) after 3 h of aging. The spectrum of blank SnO₂ colloidal suspension is also shown (spectrum c).

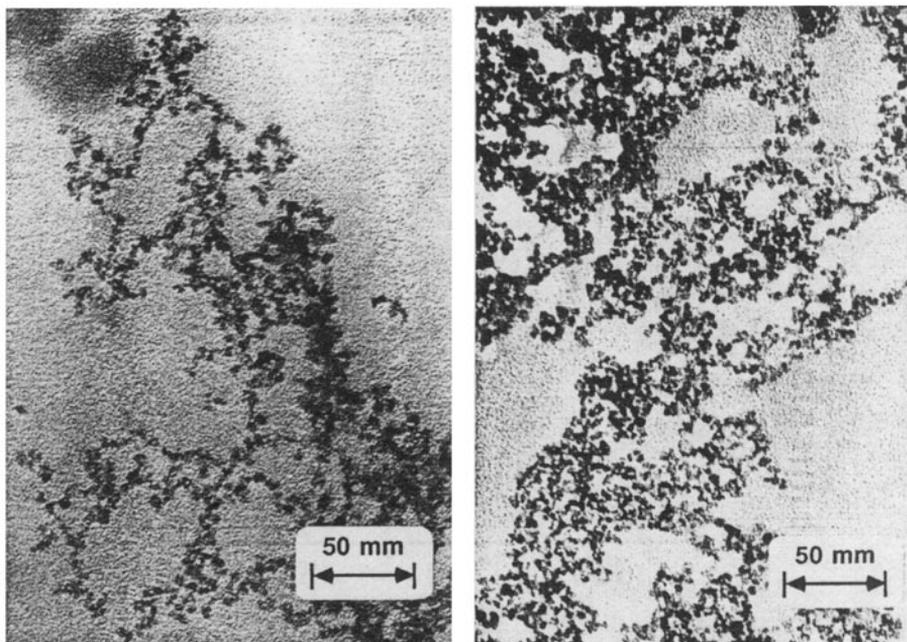


Figure 2. Transmission electron micrograph of SnO_2 colloids (560000X) and $\text{SnO}_2@ \text{CdS}$ colloids (530,000X).

capped colloids exhibit significant absorption in the visible. The onset of absorption of these colloids is at 480 nm which is close to the CdS bandgap of 2.5 eV. The change in the absorption of the aged solutions only exhibit a small shift in the onset absorption (5–10 nm) which we attribute to a small growth in the particle diameter.

b. *Transmission electron microscopy.* Figure 2 shows the transmission electron microscopy (TEM) pictures of SnO_2 and $\text{SnO}_2@ \text{CdS}$ colloids. SnO_2 colloids have particle diameters in the range of 50–70 Å. $\text{SnO}_2@ \text{CdS}$ colloids are nearly spherical with very small change in the particle diameter. This shows that the CdS layer coated onto the SnO_2 core is relatively thin. We expect its thickness to be in the range of 5–10 Å. The pictures of capped colloid samples do not show two different particle sizes, thus, the possibility of forming CdS particles away from the SnO_2 surface is ruled out. Similar observations were also made with CdS capped SiO_2 colloids. The growth of the CdS layer on SiO_2 (particle diameter 50–70 Å) was less than 10 Å. Relatively small polydispersity observed from the micrographs in figure 2 indicates that the capping of CdS is quite uniform over the oxide particles.

c. *Emission spectra.* Emission measurements of semiconductor colloids provides a convenient means of probing charge trapping, as well as interfacial charge transfer processes^{41–43}. Coadsorption of ions from solution often dictates the nature of surface states which influences trapping of the photogenerated charge carriers. The nature of surface defect sites influences the emission properties of semiconductor colloids. It would therefore be interesting to see what effect the oxide core has on the emission properties of CdS. The emission spectra of $\text{SnO}_2@ \text{CdS}$ colloids and $\text{SiO}_2@ \text{CdS}$ are shown in figures 3 and 4. The freshly prepared suspensions of both samples show red

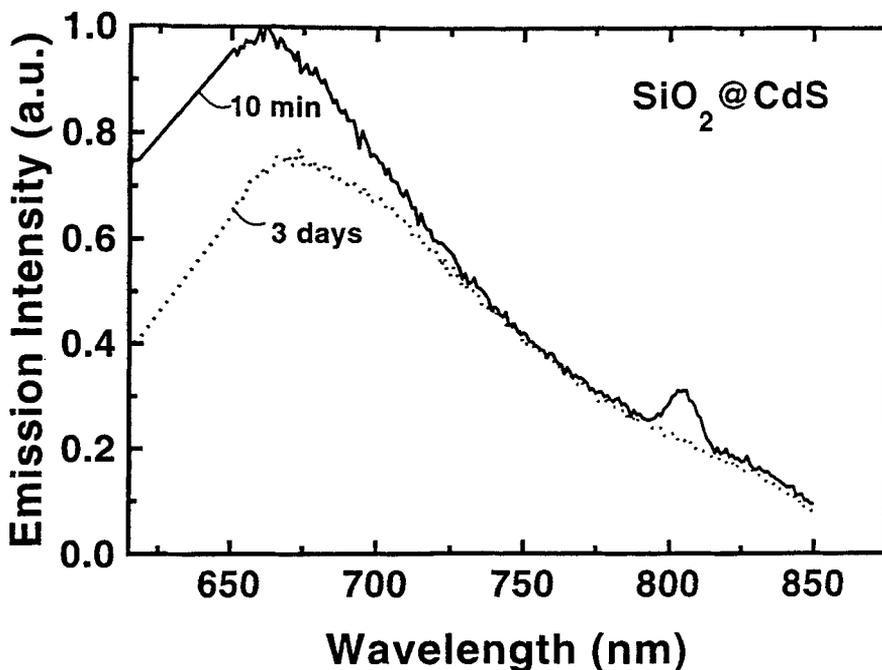


Figure 3. Emission spectra of aqueous suspensions of $\text{SiO}_2@\text{CdS}$ colloids (a) 10 min after preparation and (b) after 3 days of aging. The spectra were recorded at room temperature (296 K) with 400 nm excitation and were corrected for instrument response.


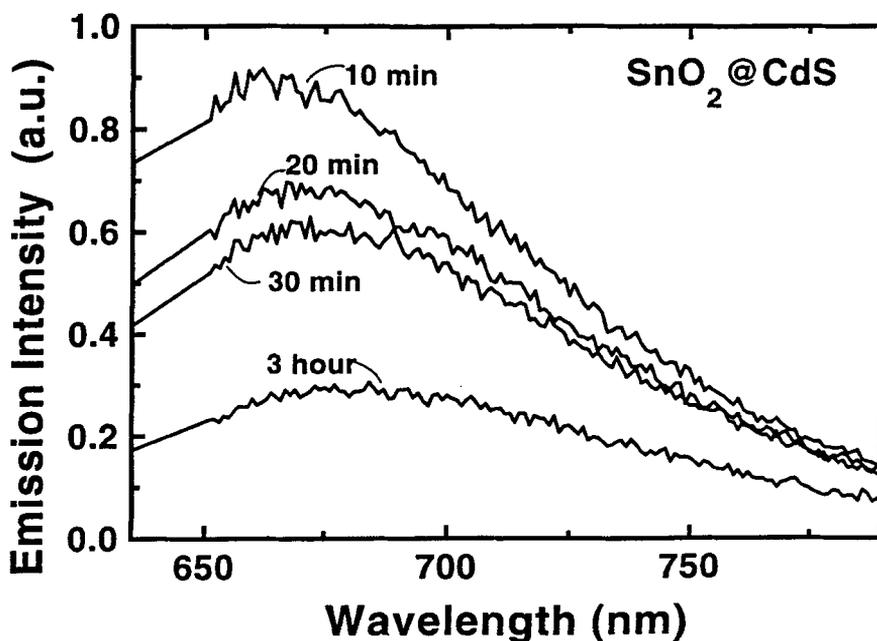


Figure 4. Emission spectra of aqueous suspensions of $\text{SnO}_2@\text{CdS}$ colloids recorded at time intervals: (a) 10 min, (b) 20 min, (c) 30 min and (d) after 3 h after its preparation. The spectra were recorded at room temperature (296 K) with 400 nm excitation and were corrected for instrument response.


emission with a maximum around 650 nm. This red emission mainly arises from the sulfur vacancy and its maximum is dependent on the particle size. Upon aging for 3 h $\text{SnO}_2@ \text{CdS}$ colloids show more than 70% quenching in the emission yield. There is no noticeable change in the emission maximum or the absorption spectrum which rules out particle growth during this period. Under similar aging conditions $\text{SiO}_2@ \text{CdS}$ do not show any noticeable changes in the emission yield. Aging for an additional period of 3 days produced a further 20% decrease in the emission yield (figure 3). This decrease is also accompanied by a small red-shift (15–20 nm) in the emission maximum, thus indicating a small growth in the particle size during this extended aging process.

The difference in quenching behavior suggests that the inner oxide core plays a significant role in controlling the emission properties of the outer CdS layer. SiO_2 being an insulator does not directly interact with CdS shell. On the other hand SnO_2 is a large bandgap semiconductor with its conduction band ($E_{\text{CB}} = -0.2$ V vs NHE) less negative than the conduction band of CdS ($E_{\text{CB}} = -1.2$ V vs NHE). Photoexcitation of CdS thus results in charge separation as the electrons are injected into the inner core of SnO_2 . Such a photoinduced charge separation has been observed earlier for composite semiconductor systems such as TiO_2 capped SnO_2 colloids²⁹ and TiO_2/CdS coupled colloids^{22,23}. Another interesting aspect is the aging period that is necessary to establish the interaction between the SnO_2 core and CdS shell. We attribute it to the formation of small individual crystallites of CdS in the early stages of precipitation. During the short aging period these CdS crystallites grow on the oxide surface to form a uniform layer, thereby maximizing the interaction with the inner core of SnO_2 . A pictorial illustration that shows the growth of the CdS shell on the SnO_2 core is shown in scheme 2.

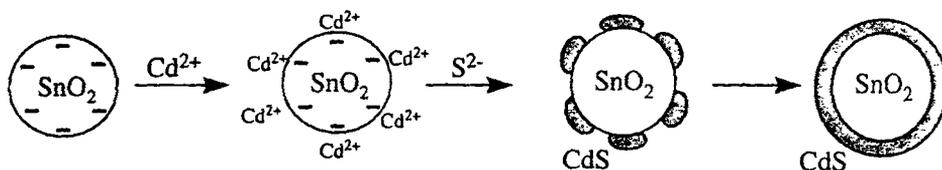


Scheme 2. Chemical precipitation of a CdS layer on to a SnO_2 nanocluster.

The emission results illustrated in figures 3 and 4 can be understood as follows. Upon bandgap excitation, the initial charge separation occurs at the CdS layer. This is followed by charge recombination and or charge separation. In the case of $\text{SiO}_2@ \text{CdS}$ the SiO_2 core has little influence on the emission behavior of the CdS shell.



On the other hand, the emission quenching in $\text{SnO}_2@ \text{CdS}$ colloids indicates lesser charge recombination as the photogenerated electrons and holes quickly diffuse in opposite directions to accumulate at the SnO_2 core and the CdS shells respectively,



The quick transfer of electrons to the SnO_2 core thus prevents the recombination of charge carriers within the CdS layer. The electron transfer between the two

semiconductors can be understood on the basis of band energetics. The energetics of the conduction ($E_{CB(SnO_2)} = -0.0$ V and $E_{CB(CdS)} = -1.0$ V vs NHE at pH 7) and valence bands ($E_{VB(SnO_2)} = +3.5$ V, $E_{VB(CdS)} = 1.5$ V vs NHE at pH 7) of these two semiconductor layers favor charge separation within the capped semiconductor system.

3.3 Picosecond laser flash photolysis experiments.

Time-resolved transient absorption spectra recorded after the 355 nm laser pulse excitation of $SiO_2@CdS$ and $SnO_2@TiO_2$ colloids are shown in figures 5 and 6 respectively. Both these spectra show intense bleaching with a maximum around 480 nm. This bleaching observed near the band edge of CdS essentially shows the shift in its absorption following photoinduced charge separation.

The nonlinear optical property of metal chalcogenide nanoclusters has been the topic of many recent investigations⁴⁴⁻⁵². In these studies explanations for the observed transient bleaching were provided on the basis of various photophysical processes, viz., dynamic Burstein effect, charge trapping and Stark effects. In a composite semiconductor system this process is more complicated as the inner semiconductor core can influence the photophysical properties of the outer layer of metal chalcogenide. Also the newly evolved electronic wave functions of the semiconductor composite can influence the overall photobleaching³⁵. Excitation of $SnO_2@CdS$ colloids results in the transfer of electrons to the inner core and the trapped holes on the outer surface.

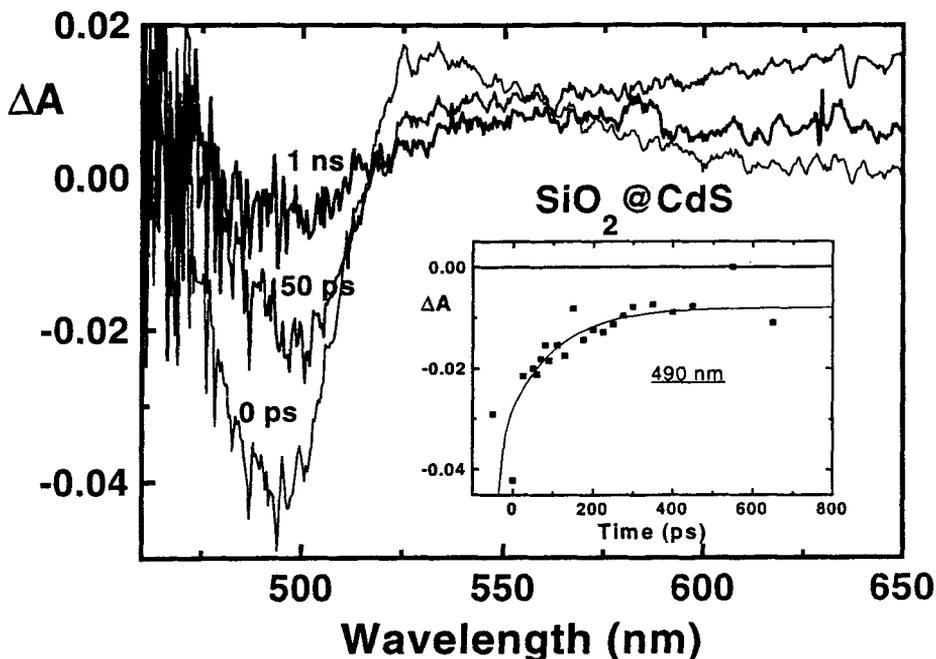


Figure 5. Time-resolved transient absorption spectra recorded after 355 nm laser excitation (1.5 mJ, 18 ps pulse width) excitation of a $SiO_2@CdS$ colloidal suspension in water (deaerated with N_2). The inset shows the transient bleaching recovery at 490 nm.

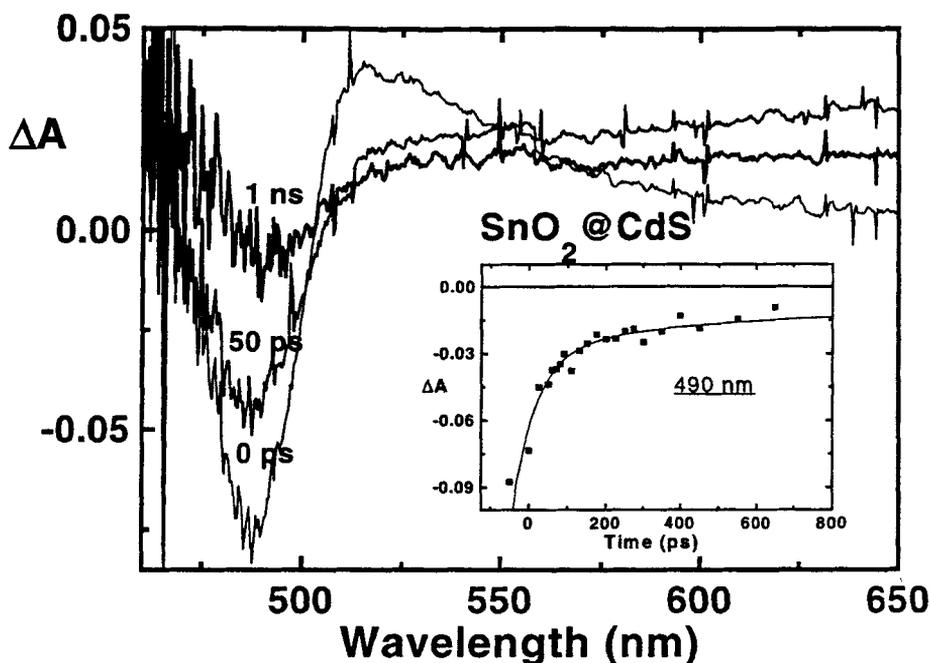


Figure 6. Time-resolved transient absorption spectra recorded after 355 nm laser excitation (1.5 mJ, 18 ps pulse width) excitation of a $\text{SnO}_2@\text{CdS}$ colloidal suspension in water (deaerated with N_2). The inset shows the transient bleaching recovery at 490 nm.

The intense electric field created as a result of this charge separation causes a shift in the band edge of CdS. This effect which is usually explained on the basis of the Stark effect has also been observed by depositing excess charge on CdS colloids or by applying an electric field to CdSe film⁵¹.

The magnitude of the bleaching in the case of $\text{SnO}_2@\text{CdS}$ is approximately two times higher than that of $\text{SiO}_2@\text{CdS}$. We attribute this enhanced bleaching to the increased charge separation in $\text{SnO}_2@\text{CdS}$ colloids. The prompt appearance of the transient bleaching indicates that this process is completed within the leading edge of the laser pulse (pulse width of 18 ps). The insets in figure 5 and 6 show the recovery of the bleaching indicating the time scale with which charges are recombined. Most of this recovery is completed within a time period of 1 ns. The residual bleaching represents long-term charge separation and/or irreversible changes resulting from the photoexcitation. These preliminary transient absorption studies indicate the possible use of capped semiconductor colloids for non-linear optical applications. We are presently carrying out femtosecond transient absorption measurements to resolve the photo-physical events that occur during the transient bleaching processes in composite semiconductor nanoclusters.

Conclusions

In this study we have made an effort to investigate photophysical properties of chemically synthesized semiconductor heterostructures such as $\text{SnO}_2@\text{CdS}$.

By controlling the methods of preparation it is possible to tailor the photocatalytic property of such composite semiconductor nanoclusters. Their ability to carry out redox processes with greater efficiency and selectivity than the single component systems has made them potential candidates for the conversion and storage of solar energy, and in the mineralization of chemical pollutants. These systems have potential applications in designing novel microheterogeneous assemblies, microelectronics and chemical sensors.

Acknowledgements

PVK acknowledges the support of the Office of the Basic Energy Sciences of the US Department of Energy. RK and GVH acknowledge the support of the Faculty Research Program of the University of Notre Dame.

References

1. Kamat P V and Vinodgopal K 1996 In *Fine Particles Science and Technology: From Micro to Nanoparticles* (ed.) E. Pelizzetti, Kluwer Academic Publishers, Dordrecht, The Netherlands, p. 303.
2. Kamat P V 1996 In *Nanocrystalline semiconductor materials* (eds) P V Kamat and D Meisel, Elsevier Science, Amsterdam
3. Nozik A J 1977 *Appl. Phys. Lett.*, **30** 567
4. Gruzdkov Y A, Savinov E N, Korolkov V V and Parmon V N 1988 *React. Kinet. Catal. Lett.*, **36** 395
5. Gerischer H and Lübke M 1986 *J. Electroanal. Chem. Interfacial Electrochem*, **204** 225
6. Vogel R, Pohl K and Weller H 1990 *Chem. Phys. Lett.*, **174** 241
7. Kohtani S, Kudo A and Sakata T 1993 *Chem. Phys. Lett.*, **206** 166
8. Vogel R, Hoyer P and Weller H 1994 *J. Phys. Chem.*, **98** 3183
9. Hotchandani S and Kamat P V 1992 *J. Phys. Chem.*, **96** 6834
10. Liu D and Kamat P V 1993 *J. Phys. Chem.*, **97** 10769
11. Liu D and Kamat P V 1993 *J. Electroanal. Chem. Interfacial Electrochem*, **347** 451
12. Hotchandani S and Kamat P V 1992 *Chem. Phys. Lett.*, **191** 320
13. Serpone N, Borgarello E and Grätzel M 1984 *J. Chem. Soc., Chem. Commun*, 342
14. Serpone N, Maruthamuthu P, Pichat P, Pelizzetti E and Hidaka H 1995 *J. Photochem. Photobiol., A: Chem.*, **85** 247
15. Vinodgopal K and Kamat P V 1995 *Environ. Sci. Technol.*, **29** 841
16. Vinodgopal K, Bedja I and Kamat P V 1996 *Chem. Mater.*, **8** 2180
17. Tennakone K, Ieperuma O A, Bandara J M S and Kiridena W C B 1992 *Semicond. Sci. Technol.*, **7** 423
18. Papp J, Soled S, Dwight K and Wold A 1994 *Chem. Mater.*, **6** 496
19. Anderson C and Bard A J 1995 *J. Phys. Chem.*, **99** 9882
20. Fu X, Clark L A, Yang Q and Anderson M A 1996 *Environ. Sci. Technol.*, **30** 647.
21. Trimoto T, Ito S, Kuwabata S and Yoneyama H 1996 *Environ. Sci. Technol.*, **30** 1275
22. Spanhel L, Weller H and Henglein A 1987 *J. Am. Chem. Soc.*, **109** 6632
23. Gopidas K R, Bohorquez M and Kamat P V 1990 *J. Phys. Chem.*, **94** 6435
24. Zhou H S, Honma I and Komiyama H 1993 *J. Phys. Chem.*, **97** 895
25. Spanhel L, Henglein A and Weller H 1987 *Ber. Bunsenges. Phys. Chem.*, **91** 1359
26. Rabani J 1989 *J. Phys. Chem.*, **93** 7707
27. Kamat P V and Patrick B 1992 *J. Phys. Chem.*, **96** 6829
28. Henglein A, Gutierrez M, Weller H, Fojtik A and Jirkovsky J 1989 *Ber. Bunsenges. Phys. Chem.*, **93** 593
29. Bedja I and Kamat P V 1995 *J. Phys. Chem.*, **99** 9182
30. Haesselbarth A, Eychmueller A, Eichberger R, Giersig M, Mews A and Weller H 1993 *J. Phys. Chem.*, **97** 5333

31. Kamalov V F, Little R, Logunov S L and El-Sayed M A 1996 *J. Phys. Chem.*, **100** 6381
32. Kietzmann R, Willig F, Weller H, Vogel R, Nath D N, Eichberger R, Liska P and Lehnert J 1991 *Mol. Cryst. Liq. Cryst.*, **194** 169
33. Evans J E, Springer K W and Zhang J Z 1994 *J. Chem. Phys.*, **101** 6222
34. Kortan A R, Hull R, Opila R L, Bawendi M G, Steigerwald M L, Carroll P J and Brus L E 1990 *J. Am. Chem. Soc.*, **112** 1327
35. Eychmueller A, Vobmeyer T, Mews A and Weller H 1994 *J. Lumin.*, **58** 223
36. Zhou H S, Sasahara H, Honma I, Komiyama H and Haus J W 1994 *Chem. Mater.*, **6** 1534
37. Zhou H S, Honma I, Haus J W, Sasabe H and Komiyama H 1996 *J. Lumin.*, **70** 21
38. Haus J W, Zhou H S, Honma I and Komiyama H 1993 *Phys. Rev.*, **47** 1359
39. Ebbesen T W 1988 *Rev. Sci. Instrum.*, **59** 1307
40. Kamat P V, Ebbesen T W, Dimitrijevic N M and Nozik A J 1989 *Chem. Phys. Lett.*, **157** 384
41. Rossetti R and Brus L 1982 *J. Phys. Chem.*, **86** 4470
42. Chestnoy N, Harris T D, Hull R and Brus L E 1986 *J. Phys. Chem.*, **90** 3393
43. Kamat P V, Dimitrijevic N M and Fessenden R W 1987 *J. Phys. Chem.*, **91** 396
44. Haase M, Weller H and Henglein A 1988 *J. Phys. Chem.*, **92** 4706
45. Henglein A, Kumar A, Janata E and Weller H 1986 *Chem. Phys. Lett.*, **132** 133
46. Banyai L and Koch S W 1986 *Phys. Rev. Lett.*, **57** 2722
47. Liu C and Bard A J 1989 *J. Phys. Chem.*, **93** 3232
48. Kamat P V, Dimitrijevic N M and Nozik A J 1989 *J. Phys. Chem.*, **93** 2873
49. Hilinski E F, Lucas P A and Wang Y 1988 *J. Chem. Phys.*, **89** 3435
50. Wang Y, Suna A, McHugh J, Hilinski E F, Lucas P A and Johnson R D 1990 *J. Chem. Phys.*, **92** 6927
51. Colvin V L and Alivisatos A P 1992 *J. Chem. Phys.*, **97** 730.
52. Luangdilok C, Lawless D and Meisel D 1996 In *Fine Particles Science and Technology* (ed.) E Pelizzatti, Kluwer Academic Publishers, Boston, p. 457