

Optical nonlinearity of organic dyes as studied by Z-scan and transient grating techniques

UMAKANTA TRIPATHY, R JUSTIN RAJESH, PREM B BISHT* and
A SUBRAHAMANYAM

Department of Physics, Indian Institute of Technology – Madras,
Chennai 600 036, India
e-mail: bisht@iitm.ac.in

Abstract. The excited state absorption cross-section of 5,5'-dichloro-11-diphenyl-amino-3,3'-diethyl-10,12-ethylnethiatricarbocyanine perchlorate (IR140) have been measured by using a single beam transmission technique. Z-scan experiments have been used to find out a few nonlinear parameters. The excited state relaxation times have also been measured by using laser induced transient grating (LITG) technique.

Keywords. Excited state absorption; Z-scan; nonlinear refractive index; excited state relaxation; transient grating.

1. Introduction

Following the absorption of the radiation the molecules can occupy the excited states. If the pump intensity is higher, then the excited molecule may absorb the light further within its fluorescence lifetime and attain a higher excited state; this phenomenon is referred to as nonlinear absorption. Measurement of nonlinear refractive index in the presence of nonlinear absorption can be done by a single beam transmission measurement method. These measurements can give the value of excited state absorption cross-section (S_{e_s}) besides other nonlinear parameters. Hercher¹ have obtained the value of S_{e_s} for a thick saturable absorber. Recently Gu *et al* have obtained the S_{e_s} value for Ni-azo chelate dye films by open aperture Z-scan technique.² The existence of excited state absorption transitions limits the maximum transmission of organic dyes to a well-defined value of less than unity.

The fluorescence lifetime of IR140 have been reported by Ganikanov *et al*³. The absorption and fluorescence characteristics of laser dye IR140 were reported by Robert Gray *et al*⁴ and the solvation dynamics of organic dye IR140 has been investigated using the transient grating technique by Vauthey *et al* by fs to ps time scale in a series of solvents.⁵

The laser induced transient grating (LITG) technique is generally used to investigate the properties of optically excited materials.^{6–8} The excited state absorption cross sections are of prime importance when dealing with the diffraction efficiency of the LITG of the dyes. The present paper deals with the experiments and the theoretical calculation of S_{e_s} and other photophysical parameters of IR140. Rhodamine 6G has also been used as a standard. The experiments are based on a single beam transmission measurement method for S_{e_s} calculations. For nonlinear parameter estimation we have used the Z-scan

*For correspondence

technique. The decay profiles have been measured by LITG method. The excited state relaxation times have been calculated by fitting the decay curve.

2. Theory

2.1 Effects of nonlinearity

For a fast third order nonlinearity the index of refraction \mathbf{h} is expressed in terms of nonlinear refractive indices \mathbf{h}_2 (esu) through⁹

$$\mathbf{h} = n_0 + \mathbf{h}_2 / 2[|\bar{E}|^2] = n_0 + \Delta n, \quad (1)$$

where n_0 is the linear refractive index, \bar{E} is the peak electric field.

The amplitude and phase of the electric field as a function of distance (z) are governed by (2) and (3)

$$\frac{d\Delta\mathbf{f}}{dz} = \Delta n(I)k, \quad (2)$$

and

$$\frac{dI}{dz} = -\mathbf{a}I - \mathbf{s}_{es}N_{es}I, \quad (3)$$

where dz is the differential element of depth in the sample and (3) contains both linear (\mathbf{a}) and nonlinear ($\mathbf{s}_{es}N_{es}$) absorption terms. Solving the equations in case of a third order nonlinearity and neglecting nonlinear absorption the instantaneous on-axis phase shift at focus is defined as^{9,10}

$$\Delta\mathbf{f}_0(t) = k \cdot \Delta n_0(t)L_{\text{eff}}, \quad (4)$$

where $L_{\text{eff}} = (1 - \exp(-\mathbf{a}L))/\mathbf{a}$ is the effective length of the sample, in which L is the length of the sample. $\mathbf{D}_0(t)$ is the change in refractive index which is dependent on the fluence. The time averaged $\langle \Delta\mathbf{f}_0(t) \rangle$ is related to the time-averaged index change $\langle \Delta n_0(t) \rangle$ through (4) for transient effect.

The average value of the third order nonlinear refractive index (\mathbf{h}_2) can also be determined by^{2,10}

$$\mathbf{h}_2(\text{esu}) = [(\sqrt{2}cn_0\mathbf{I})/(80\mathbf{p}^2I_0L_{\text{eff}})]\Delta\mathbf{f}_0, \quad (5)$$

where I_0 is the peak on axis irradiance at focus, c is the velocity of light and \mathbf{I} is the wavelength of the laser.

The on axis phase shift at the focus ($\Delta\mathbf{f}_0$) can be obtained from the numerical fitting of the closed aperture data with¹¹

$$T = 1 + [4x/(x^2 + 9)(x^2 + 1)]\Delta\Phi_0 - [2(x^2 + 3)/(x^2 + 9)(x^2 + 1)]\Delta\mathbf{y}_0, \quad (6)$$

Here $\Delta\mathbf{y}_0$ is the on-axis phase shift due to nonlinear absorption and $x = z/z_0$, where z_0 is the Rayleigh range. The ratio of $\Delta\mathbf{y}_0$ and $\Delta\mathbf{f}_0$ is known as coupling factor (\mathbf{r}). It also

relates the real and imaginary parts of third order nonlinear susceptibility.¹¹ However, in the absence of the nonlinear absorption the second term in (6) can be neglected.¹¹

2.2 Excited state absorption cross-section

The ground state absorption cross-section (s_3) can be calculated by using Beer-Lambert's law. The σ_{es} value can be determined with the help of three and four level energy systems given in figure 1a and b¹ by varying the input intensity of the laser beam. The steady state transmission of a thick sample is given by

$$dI/dz = -I(\mathbf{a} + \mathbf{b}) = -I[(\mathbf{a} + \mathbf{b}(I/I_s))/(1 + I/I_s)]. \tag{7}$$

The solution to the differential equation (7) (at $z = 0, I = I_0$) is given by

$$\ln T - \ln T_0 = (\mathbf{g} - 1) \ln((\mathbf{g} + I_0/I_s)/(\mathbf{g} + T I_0/I_s)), \tag{8}$$

where \mathbf{g} is defined as

$$\mathbf{g} \equiv \mathbf{a}/\mathbf{b} \equiv s_3/s_{es}. \tag{9}$$

By fitting the experimental data (in the graph T vs I_0/I_s) for the numerical solution of (8) by Newton-Ralphson method, we can find out the value of \mathbf{g} . By using the value of \mathbf{g} and s_3 , we can calculate the value of s_{es} from (9).

2.3 Diffraction efficiency and excited state relaxation times

Diffraction efficiency of the thin grating is experimentally measured by taking the ratio of the intensity of the diffracted signal to that of the transmitted intensity of one of the

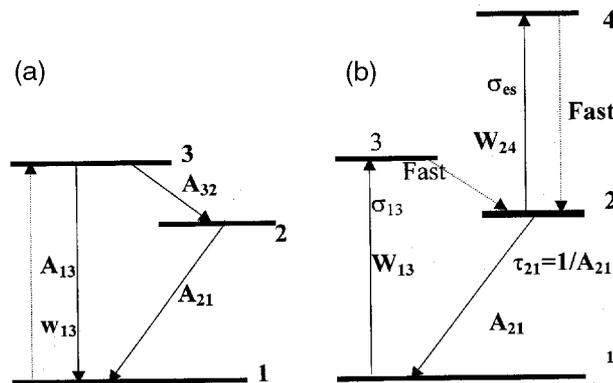


Figure 1. Energy schemes describing the excited state absorption cross-section with the help of three- (a) and four-level (b). A_{21} is the transition probability from level 2 to level 1, W_{13} is the rate of absorption from level 1 to level 3 and W_{24} is the rate of absorption from level 2 to level 4.

laser beams producing the grating.⁶ The time profiles obtained from the LITG experiment may contain several contributions such as the coherence spike, optical Kerr effect of the solvent (OKE), density phase grating, acoustic grating and relaxation times of the molecules.¹²⁻¹⁸ As a result the observed decay follows a complex equation.^{13,15} However, by excluding the longer part of the decay (fluorescence lifetime) as well as the coherence spike, the estimation of the excited state relaxation times can be done.¹⁹

3. Experimental

The experimental setup for the transmittance measurement as a function of incident intensity is shown in figure 2a. A frequency doubled mode-locked Nd:YAG laser (Continuum Model YG601, 35 ps, 532 nm, 10 Hz) was used as the light source. The radius of the beam waist (w_0) was 4.1 mm. The transmitted energy through the sample was measured by a PMT in the far field.^{1,20,21} For the measurement of other nonlinear parameters the Z-scan experimental setup is shown in figure 2(b). An Argon ion laser ($\lambda = 514.5$ nm, power = 20 mW) was used as the light source. The measurement includes the transmittance measurement as a function of the position of the sample by using a positive lens having focal length $f = 20$ cm. This measurement is known as Z-scan technique. The radius of the beam waist (w_0) in this case was 68.6 μm with a corresponding Rayleigh range of 2.87 cm. The transmitted energy is measured by a PMT in the far field. Approximate care was taken against the surface imperfections in the sample that may lead to systematic transmittance trace change, which could mask the effect of nonlinear refraction.^{4,22} The experimental setup given in figure 2b is known as closed aperture Z-scan setup, while an identical setup without the aperture is known as open aperture Z-scan setup which gives σ_{es} value exclusively. The details of the experimental setup for creation and detection of the LITG are given elsewhere.¹⁹ The solvents viz., dimethyl sulphoxide (DMSO), methanol (MeOH), ethylene glycol (Et Gly) of spectrograde quality were used as received.

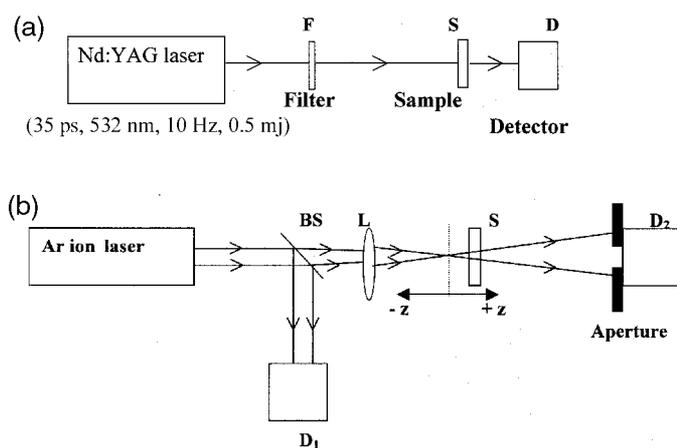


Figure 2. Experimental arrangement (a) for the measurement of excited state absorption cross-section: F – Filter, S – Sample, D – Detector; and (b) for Z-scan technique: D₁ and D₂ – Detectors, BS – Beam splitter, L – lens, S – sample and Z – sample position.

4. Results and discussions

4.1 Measurement of S_{es}

The photophysical parameters of the dyes are given in table 1. Figure 3 shows a result obtained from the energy dependence of the transmission. At lower intensities (region A),

Table 1. Photophysical parameters for laser dyes.

Dyes and solvents	Peak value (nm)		S_{13} ($\times 10^{-16}$) cm^2	S_{es} ($\times 10^{-18}$) cm^2	t_F	t_{or}	Sign of \mathbf{h}_2	\mathbf{c}^3 esu
	I_{ABS}	I_{EMISS}						
<i>R6G</i>								
MeOH and Et. Gly. (1:1)	530	562	1.6	3.73	231 ± 64 ps	150 ± 24 ps	Negative	
DMSO PMMA ^a								
<i>IR140</i>								
DMSO	820	837 ^b	24.8	3.73	231 ± 64 ps	288 ± 8 fs ³	Negative ^{c d}	
MeOH	800 ⁴	830 ⁴						
Et. Gly					165 ± 5 ps ³			
Et. Gly and DMSO (1:1)					240 ps ³			

^a Polymethyl methacrylate (PMMA)

^b The solvent is MeOH + DMSO (1:1)

^c The value of $\mathbf{h}_2 \approx -(3.73 \pm 0.06) \times 10^{-4}$ esu

^d The real value of $\mathbf{c}^{(3)}$ i.e. $\mathbf{c}_R^{(3)} = -(1.0 \pm 0.02) \times 10^{-12}$ m²/V²

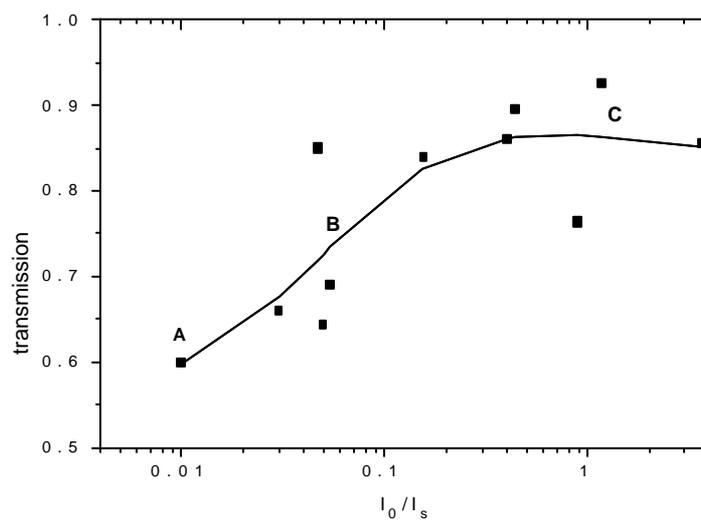


Figure 3. Plot of I_0/I_s vs transmission intensity for IR140 in DMSO for the calculation of excited state absorption cross-section. The parameters are: Concentration is 2.5×10^{-4} M, $\lambda = 532$ nm, $t_p = 35$ ps and $S_{es} = 3.73 \times 10^{-18}$ cm².

the transmission shows low values corresponding to a small signal transmission (T_0), followed by a region B where the transmission increases. In third region the transmission is high and approaches unity (region C). Region A is the linear absorption region, here the transmission follows the Beer's law, i.e. the effect of the absorptive transition between excited states is negligible. In region B as we increase the incident energy of laser pulse the molecules in the thermal equilibrium position of first excited state (level 2 of figure 1b) absorb the energy and go to the higher excited state (level 4 of figure 1(b)). Here the term \mathbf{s}_{es} comes in to picture. The region C is known as residual absorption,¹ which is a nonsaturable component of the absorption. The obtained transmission curve was simulated with the theoretical formulation developed in §2, which gives the value of \mathbf{s}_{es} for this system.

4.2 Measurement of (\mathbf{h}_2)

In the Z-scan experiment the translation of the sample leads to change of the incident intensity falling on the sample, which results in a change in the refractive index (\mathbf{h}_2) of the sample. The sign as well as the magnitude of \mathbf{h}_2 for the dye IR140 can be determined by measuring the transmission through the circular aperture after the sample.²²

Figure 4 shows the experimental result for IR140 in solvent DMSO obtained by closed aperture Z-scan technique. A prefocal transmittance maximum (peak) followed by a post-focal transmittance minimum (valley) in the Z-scan experiment is a signature of negative refractive nonlinearity. Following the same analogy, a positive nonlinear refraction gives rise to an opposite valley-peak configuration. The Z-scan signature for the organic dye

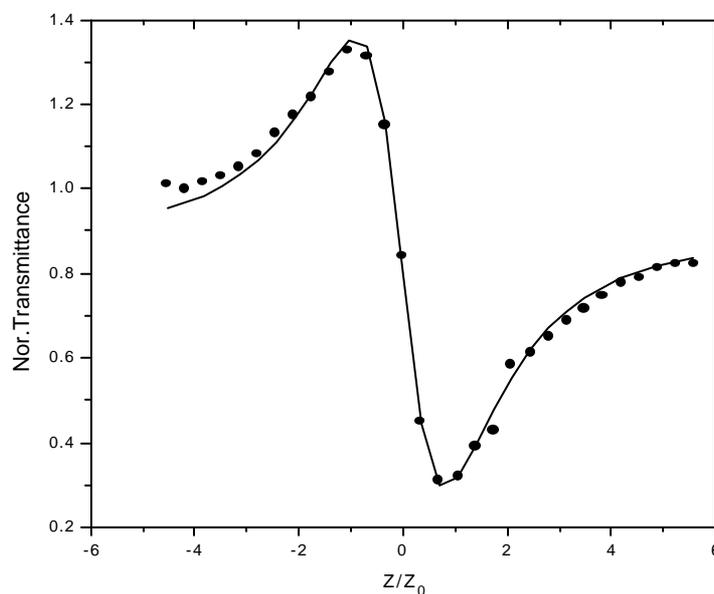


Figure 4. Plot for z/z_0 vs normalized transmittance for IR140 (1×10^{-4} M) in DMSO. The parameters are: $\lambda = 514.5$ nm, Power = 20 mw, $\Delta T_{p-v} = 1.02$, $\Delta f_0 = -(2.62 \pm 0.04)$ and the coupling factor $r = -(0.06 \pm 0.01)$.

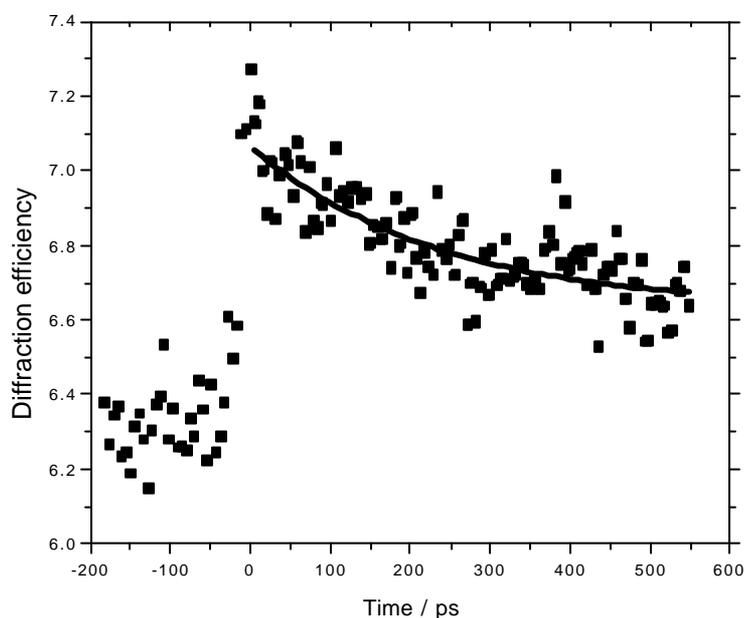


Figure 5. Decay curves for IR140 (2.5×10^{-4} M) in DMSO. The fitted line for a single exponential decay function for a limited range is also shown. The parameters are: $\lambda = 532$ nm, $t_p = 35$ ps and $t_f = 231 \pm 64$ ps.

IR140 in DMSO shows negative refractive nonlinearity. The value of the transmission from peak to valley (ΔT_{p-v}) is 1.02 and the on axis phase shift at the focus ($\Delta \mathbf{f}_0$) is obtained as $-(2.62 \pm 0.04)$, which gives an index change of $\langle \Delta n_0 \rangle = -(3.53 \pm 0.06) \times 10^{-4}$. This value of $\langle \Delta n_0 \rangle$ corresponds to the value of $\mathbf{h}_2 \approx -(3.73 \pm 0.06) \times 10^{-4}$ esu. The real part of the third order nonlinear susceptibility has a value of $\mathbf{c}_R^{(3)} = -(1.0 \pm 0.02) \times 10^{-12}$ m²/V². From the method described in ref. [11] we have obtained the value of \mathbf{r} as $-(0.06 \pm 0.01)$.

4.3 Measurement of relaxation time

The decay profiles of the grating formed by the pump beams at lower pump energy (< 0.14 mJ) for the IR140 in DMSO is shown in figure 5. The observed decay profile shows a sharp peak at short time followed by a decaying component. The sharp peak at zero time is known as the coherence spike, which occurs in LITG due to the diffraction of one pump pulse from the grating formed between the probe pulse and the other pump pulse at time zero. The coherence spike appears only when the pump and the probe beams are derived from the same laser. A Gaussian profile with a half-width equal to that of the pump laser pulse accounts for this.^{15,16} The decay curves can have a varying nature depending upon the polarisation of the pump and probe beams, intensity of the incoming beams and wavelength of probe beam. By fitting the limited range of the decay curve with a single exponential function a rough estimate of the excited state relaxation time of the molecules in the solvent can be obtained. We obtained average value of t_{or} as 150 ± 24 ps for R6G in DMSO, which is in close agreement with the value obtained from

Debye–Stokes–Einstein²³ hydrodynamic theory. By using the same experimental setup we obtained the value of the lifetime of the decay of IR140 in the solvent DMSO. The value of the decay constant is 231.8 ± 64.8 ps which is equal to the fluorescence lifetime of IR140.⁵ The orientational relaxation time of IR140 in solvent EtGly is 288 ± 8 fs⁵ which will be buried in the coherence spike in our case.

5. Conclusions

We have investigated the excited state absorption cross-section of the organic dye IR140 by a single beam transmittance measurement as a function of incident intensity. The non-linear transmittance was found fluence dependent on picosecond time scale at 532 nm. The calculated σ_{es} for IR140 in DMSO is 3.73×10^{-18} cm². The excited state relaxation time in DMSO was found to be 231 ± 64 ps. From Z-scan experiment, it is observed that IR140 has negative refractive nonlinearity.

Acknowledgments

We thank Council of Scientific and Industrial Research, New Delhi and Department of Science and Technology, New Delhi for financial assistance.

References

1. Hercher M 1967 *App. Opt.* **6** 947
2. Gu Y Z, Gan F X, Wang S Q and Xu H J 2001 *Opt. Commun.* **197** 501
3. Ganikhanov F, Hsieh J-M, Ci-Ling Pan 1995 *Opt. Commun.* **114** 289
4. Gray R, Walton D, Bikerton J, Richards P and Heptinstall J 1996 *Dyes Pigments* **30** 321
5. Gumy J C, Nicolet O and Vauthey E 1999 *J. Phys. Chem.* **A103** 10737
6. Eichler H J, Gunter P and Pohl D W 1986 *Laser induced dynamic gratings* (ed.) T Tamir (Berlin: Springer-Verlag) vol. 50
7. Bisht P B 2001 *Res. Chem. Intermed.* **27** 539
8. Rajesh R J, Bisht P B 2002 *Chem. Phys. Lett.* **357** 420
9. Bahae M S, Said A A and Van Stryland E W 1989 *Opt. Lett.* **14** 955
10. Bahae M S, Said A A, Wei T-H, Hagan D J and Van Stryland E W 1990 *IEEE J. Quant. Electron.* **26** 760
11. Liu X, Guo S, Wang H and Hou L 2001 *Opt. Commun.* **197** 431
12. Gumy J-C and Vauthey E 1997 *J. Phys. Chem.* **A101** 8575
13. Gumy J-C, Nicolet O and Vauthey E 1999 *J. Phys. Chem.* **A103** 10737
14. Terazima M 1998 *Adv. Photochem.* **24** 255
15. Degg F W D and Fayer M D 1989 *J. Chem. Phys.* **91** 2269
16. Mayers A B, Hochstrasser R M 1986 *IEEE J. Quant. Electron.* **22** 1482
17. Salcedo J R, Siegman A E, Dlott D D and Fayer M D 1978 *Phys. Rev. Lett.* **4** 131
18. Eichler H J, Langhans D and Massman F 1984 *Opt. Commun.* **50** 117
19. Rajesh R J, Natarajan T S and Bisht P B 2001 *Indian J. Pure Appl. Phys.* **39** 636
20. Hammand P R 1979 *IEEE J. Quant. Electron.* **15** 624
21. Falkenstein W, Penzkofer A and Kaiser W 1978 *Opt. Commun.* **27** 151
22. Gunter P 2000 *Nonlinear optical effects and materials* (ed.) P Gunter (Springer Verlag) ch. 2.5.2, vol. 72, p. 106
23. Fleming G R 1986 *Chemical applications of ultrafast spectroscopy* (New York: Oxford University Press) ch. 6, p. 124
24. Bisht P B, Fukuda K and Hirayama S 1996 *J. Chem. Phys.* **105** 9349